

**VIKASH POLYTECHNICBARGARH**  
**DEPARTMENT OF CIVIL ENGINEERING**



**LECTURE NOTE ON: STRUCTURAL DESIGN - I**  
**(TH-1) 4<sup>TH</sup> SEMESTER**

**PREPARED BY: MRS PRATIBHA PRADHAN**  
**SR. LECTURER IN CIVIL**  
**ENGINEERING DEPT**  
**VIKASH POLYTECHNIC,BARGARH**

## WORKING STRESS METHOD

### Objective of design and detailing:

Every structure must be **designed** to satisfy three basic requirements;

- **Stability** to prevent overturning, sliding or buckling of the structure, or parts of it, under the action of load.
- **Strengths** to resist safely the stresses induced by the loads in the various structural members.
- **Serviceability** to ensure satisfactory performance under service load condition. Serviceability includes two parameters i.e deflection and cracking. The deflection should be limited to ensure the better appearance of the structure and to prevent cracking. The cracking of the reinforced concrete should not be excessive to ensure better appearance and also to prevent the access of water from cracks which may corrode the reinforcement.

There are two other considerations that a sensible designer ought to bear in mind, viz. **economy** and **aesthetics**.

### Different methods of design:

#### (a) Working stress method:

- The earliest codified design philosophy is that of **working stress method** of design (WSM).
- Close to a hundred years old, this traditional method of design, based on linear elastic theory is still surviving in a number of countries.
- In WSM it is assumed that structural material e.g. concrete and steel behave in linearly elastic manner and adequate safety can be ensured by restricting the stresses in the material induced by working loads (service loads) on the structure.
- As the specified permissible (allowable) stresses are kept well below the material strength, the assumption of linear elastic behavior considered justifiable.
- The ratio of the strength of the material to the permissible stress is often referred to as the factor of safety.

#### (b) Ultimate load method:

- In this method the inelastic behavior of concrete is taken into account and therefore reserve strength of concrete can be used leading to the economical design.
- In design, the loads on the structure are increased by suitable load factor and the structure is loaded with these increased loads called ultimate load.
- For material (steel and concrete) the ultimate behavior is taken into account.
- The ultimate load method leads the designer to economy but at the same time, to very slender section, larger deflection and larger crack width in concrete.

**(c) Limit state method:**

- In this method the design based on limit state concept, the structure shall be designed to withstand safely all loads liable to act on it through out its life.
- It shall also satisfy the serviceability requirement such as prevention of excessive deflection and cracking.
- WSM gives satisfactory performance of the structure at working loads and it is unrealistic at ultimate state of collapse.
- ULM provides realistic assessment of safety but it does not guarantee the satisfactory serviceability requirement at service load.
- The acceptable limit for the safety and serviceability requirement before failure occurs is called “limit state”
- The aim of the design is to achieve acceptable probabilities that the structure will not become unfit for the use for which it is intended, that means it will not reach a limit state. For ensuring the above objective, various partial factor of safety are employed in the limit state design.
- The design values are obtained from the characteristic values through the use of partial factor of safety. Design loads are obtained by multiplying a partial factor of safety for loads with characteristic load and in a similar manner the design strength of material are obtained by dividing the characteristic strength with respective partial factor of safety for materials.

**Reinforced cement concrete:**

- It is a combination of concrete and steel to build a structure instead of using only concrete.
- Concrete is good in resisting compression but is weak in resisting tension.
- On the otherhand steel has high tensile strength and the bond between concrete and steel is good.
- To overcome the drawback of concrete, steel bars are used alongwith concrete.

**Grades of concrete:**

- The properties of concrete vary so much with composition and method of mixing therefore different types of concrete can be obtained.
- Concrete mixes have been classified into various grades by the Indian Standard Institution.

Type of concrete	Grade designation	Characteristic compressive strength at 28 days in N/mm <sup>2</sup>
Normal strength concrete	M5	5

	M10	10
	M15	15
Standard concrete	M20	20
	M25	25
	M30	30
High strength concrete	M35 onwards	35

- In this designation M refers to mix and the number represents the characteristic compressive strength of cube at 28 days expressed in  $\text{N/mm}^2$
- Characteristic strength is defined as the strength of the material below which not more than 5% of the test results are expected to fall.

#### **Advantages of reinforced cement concrete:**

- Reinforced Cement Concrete has good compressive strength (because of concrete).
- RCC also has high tensile strength (because of steel).
- It has good resistance to damage by fire and weathering (because of concrete).
- RCC protects steel bars from buckling and twisting at the high temperature
- RCC prevents steel from rusting
- Reinforced Concrete is durable
- The monolithic character of reinforced concrete gives it more rigidity.
- Maintenance cost of RCC is practically nil.

#### **Concept of under, balanced and over reinforced beam section:**

##### **Under reinforced section:**

- In some cases a larger section provided than required for a balanced section. In other words, a smaller area of steel is provided than required for a balanced section.
- In this case at some value of loads, the stress in steel will reach at its permissible or design value and fails while concrete stress is less than its permissible value.
- The failure in this case is a tension or ductile failure.

##### **Balanced reinforced section:**

- In this type of design, the section is so proportioned that the steel and concrete both reach their maximum values of stress at the same time. Thus at some value of load both the material will fail at the same time.

##### **Over reinforced:**

- In this case steel area provided is more than the area required for a balanced section.
- At some value of load the stress in concrete will reach at its permissible value and fails while stress

in steel is less than its permissible value.

- The failure in this case is called compression failure and therefore it will be a brittle failure.

### Working stress method:

#### Assumptions :

The analysis and design of a RCC member are based on the following assumptions


- Concrete is assumed to be homogeneous
- At any cross section, plane sections before bending remain plane after bending.
- The stress-strain relationship for concrete is a straight line, under working loads
- The stress-strain relationship for steel is a straight line, under working loads
- Concrete area on tension side is assumed to be ineffective
- All tensile stresses are taken up by reinforcements and none by concrete except when specially permitted.
- The steel area is assumed to be concentrated at the centroid of the steel.
- The modular ratio has the value  $280/3\sigma_{cbc}$  where  $\sigma_{cbc}$  is permissible stress in compression due to bending in concrete in  $\text{N/mm}^2$  as specified in code (IS:456-2000).

#### Permissible stresses:

- In working stress method, the stresses in materials are not exceeded beyond their permissible values. The permissible stresses are found by using suitable factor of safety to the material strength.
- For concrete in compression in bending a factor of safety equal to 3 is considered on characteristic strength of concrete.
- For steel a factor of safety equal to 1.8 is considered on a yield strength of steel in tension due to bending.

#### Derivation of formula for balanced design:

Consider a singly reinforced beam with stress and strain diagram as shown in figure:

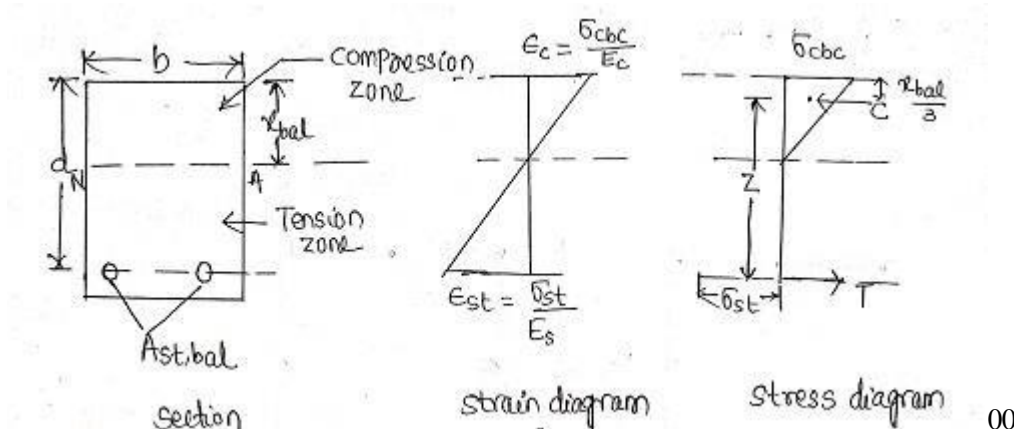

$A_{st,bal}$  = reinforcement area provided for balanced section

$\sigma_{cbc}$  = permissible stress in concrete in bending compression

$\sigma_{st}$  = permissible stress in steel in tension

$E_c$  = modulus of elasticity of concrete

$E_s$  = modulus of elasticity in steel

$\epsilon_c$  = strain in concrete in extreme compression fibre =  $\sigma_{cbc}/E_c$

$\epsilon_{st}$  = strain in steel =  $\sigma_{st}/E_s = \sigma_{st}/mE_c$

$b$  = width of beam

$d$  = effective depth which is defined as the distance from extreme compression fibre to the centroid of tensile reinforcement

$x$  = depth of N.A which is defined as the distance of neutral axis from extreme compression fibre.

$z$  = lever arm which is defined as the distance between centroid of compressive force to the centroid of tensile force

**To find Neutral axis :**

From the strain diagram

$$\frac{x_{bal}}{d-x_{bal}} = \frac{\sigma_{cbc}/E_c}{\sigma_{st}/E_s} = \frac{m\sigma_{cbc}}{\sigma_{st}}$$

$$X_{bal} = \frac{m\sigma_{cbc}}{m\sigma_{cbc} + \sigma_{st}} d = \frac{1}{1 + \frac{\sigma_{st}}{m\sigma_{cbc}}} d$$

$$X_{bal} = kd$$

$$\text{Where } k = \frac{1}{1 + \frac{\sigma_{st}}{m\sigma_{cbc}}}$$

and is known as neutral axis constant

**To find lever arm:**

From stress diagram

$$\begin{aligned} Z &= d - \frac{x_{bal}}{3} \\ &= d - \frac{kd}{3} = \left(1 - \frac{k}{3}\right)d \\ &= jd \end{aligned}$$

$$\text{Where the constant } j = \left(1 - \frac{k}{3}\right)$$

And is known as lever arm constant

**To find total forces:**

$C$  = total compression

$T$  = total tension

$$\begin{aligned} C &= \frac{1}{2} \sigma_{cbc} b x_{bal} \\ &= \frac{b x_{bal} \sigma_{cbc}}{2} \end{aligned}$$

$$T = \sigma_{st} A_{st, bal}$$

**To find moment of resistance of section**

Capacity of a section to resist the moment is known as its moment of resistance.

$M.R = \text{total compressive force} \times \text{lever arm}$

Or,

$M.R = \text{total tensile force} \times \text{lever arm}$

Considering compressive force

$M.R = \text{total compression} \times \text{lever arm}$

$$= (\frac{1}{2} \sigma_{cbc} b x_{bal}) j d$$

$$= (\frac{1}{2} \sigma_{cbc} b k d) j d$$

$$= (\frac{1}{2} \sigma_{cbc} k j) b d^2$$

$$M = Q_{bal} b d^2$$

Where  $Q_{bal} = \frac{1}{2} \sigma_{cbc} k j$  and is known as moment of resistance factor

Considering the tensile forces

$M.R = \text{total tension} \times \text{lever arm}$

$$= A_{stbal} \sigma_{st} j d$$

### To find steel area

For a balanced section

$$M_{bal} = A_{stbal} \sigma_{st} j d$$

$$A_{stbal} = \frac{M_{bal}}{\sigma_{st} j d}$$

Percentage steel =  $p_t = 100 A_{st} / b d$

For a balanced section  $p_{tbal} = 100 \times \frac{A_{stbal}}{b d} = 100 \times \frac{M_{bal}}{\sigma_{st} j d} \times \frac{1}{b d}$

$$P_{tbal} = \frac{100 \times \frac{1}{2} \sigma_{cbc} \times k \times j \times b d \times d}{\sigma_{st} \times j d \times b d} = \frac{50 \sigma_{cbc} \times k}{\sigma_{st}}$$

To design balanced section

For a given design moment  $M$ , consider  $M = M_{bal}$

If width of beam is assumed

$$d = \sqrt{\frac{M_{bal}}{b Q_{bal}}}$$

$$\text{steel area} = A_{st} = A_{stbal} = \frac{M}{\sigma_{st} j d}$$

### Question 1

Calculate the design constants for the following material considering the balanced design for singly reinforced section. The materials are M20 grade concrete and mild steel reinforcement.

Solution:

For M20 grade concrete,  $\sigma_{cbc} = 7 \text{ N/mm}^2$

For Fe250 grade steel,  $\sigma_{st} = 140 \text{ N/mm}^2$

$$\text{Modular ratio} = m = \frac{280}{3 \sigma_{cbc}} = \frac{280}{3 \times 7} = 13.33$$

$$\text{Neutral axis constant} = k = \frac{1}{1 + \frac{\sigma_{st}}{m\sigma_{cbc}}} = \frac{1}{1 + \frac{140}{13.33 \times 7}} = 0.4$$

$$\text{Lever arm constant} = j = \left(1 - \frac{k}{3}\right) = \left(1 - \frac{0.4}{3}\right) = 0.87$$

$$\text{M.R constant} = Q_{bal} = \frac{1}{2}\sigma_{cbc}kj = \frac{1}{2} \times 7 \times 0.4 \times 0.87 = 1.21$$

$$P_{tbal} = \frac{50\sigma_{cbc} \times k}{\sigma_{st}} = \frac{50 \times 7 \times 0.4}{140} = 1.0$$

### Question 2 :

For a rectangular beam of size 250 mm wide x 520 mm effective depth, find out the balanced depth of neutral axis, balanced lever arm, balanced moment of resistance and balanced steel area. The materials are M20 grade concrete and HYSD reinforcement of grade Fe 415.

Solution:

$$b = 250 \text{ mm}$$

$$d = 520 \text{ mm}$$

$$\sigma_{cbc} = 7 \text{ N/mm}^2$$

$$\sigma_{st} = 230 \text{ N/mm}^2$$

$$k = 0.29$$

$$j = 0.90$$

$$Q_{bal} = 0.91$$

$$\text{Depth of neutral axis} = kd = 0.29 \times 520 = 150.8 \text{ mm}$$

$$\text{Lever arm} = jd = 0.9 \times 520 = 468 \text{ mm}$$

$$\text{M.R of balanced section} = M = Q_{bal}bd^2 = 0.91 \times 250 \times 520 \times 520 \times 10^{-6} = 61.52 \text{ KNm}$$

$$A_{stbal} = \frac{P_{tbal} \times bd}{100} = \frac{0.44 \times 250 \times 520}{100} = 572 \text{ mm}^2$$

### Question 3

A simply supported rectangular beam of 4m span carries a uniformly distributed load of 26 KN/m . The width of the beam is 230 mm. find the depth and steel area for balanced design. Use M20 grade concrete and mild steel reinforcement.

Solution :

$$\begin{aligned} \text{Maximum moment } M &= 26 \times 4^2 / 8 \\ &= 52 \text{ Kn.m} \end{aligned}$$

$$\text{For balanced section } Q_{bal} = 1.21$$


$$\text{Effective depth required} = d = \sqrt{\frac{M_{bal}}{bQ_{bal}}} = \sqrt{\frac{52 \times 10^6}{1.21 \times 230}} = 432.3 \text{ mm}$$

$$\text{Steel area} = A_{stbal} = \frac{M}{\sigma_{st}jd} = \frac{52 \times 10^6}{140 \times 0.87 \times 432.3} = 988 \text{ mm}^2$$

Provide 5 nos. of 16 mm diameter bars giving area of  $5 \times 201 = 1005 \text{ mm}^2$

### Transformed area method:

- A transformed section is a section in which the steel area is replaced by an equivalent concrete area.
- A transformed section consists of a single material, therefore, theory of simple bending can be applied.
- The transformed section may be of steel when concrete is replaced by steel or it may be of concrete when steel area is replaced by concrete. It is usual to replace steel area by concrete, hence a transformed section would mean to a homogenous concrete section.
- The actual concrete in tension zone is absent because we have assumed that concrete carry tensile force. Thus all tensile forces will be carried by steel.

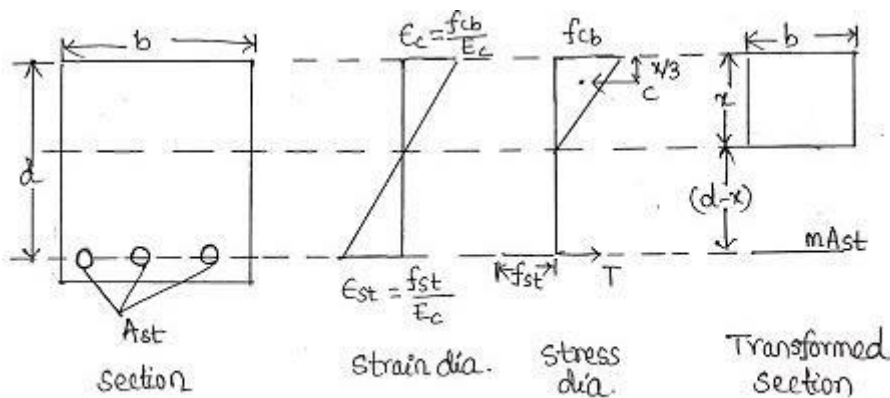

At the centroid of steel reinforcement, the surrounding concrete being elastic and having perfect bond with steel

Strain in steel = strain in concrete

Let  $f_{st}$  and  $f_{cb}$  be the stresses in steel and concrete respectively at the level of centroid of steel.

Strain in concrete = strain in steel

$$\frac{f_{cb}}{E_c} = \frac{f_{st}}{E_s} = f_{st} = m f_{cb}'$$

$$\text{Now force in steel} = A_{st} f_{st} = A_{st} m f_{cb}' \text{ ----- (1)}$$

If this steel is to be replaced by an equivalent concrete area, the equivalent concrete will carry the same force

$$\text{Now the force in equivalent concrete} = \text{transformed area} \times f_{cb}' \text{ ----- (2)}$$

Equating (1) & (2)

$$\text{Transformed area} \times f_{cb}' = A_{st} m f_{cb}'$$

$$\text{Transformed area} = m A_{st}$$

**To find neutral axis:**

$$b \times x \times (x/2) = m A_{st} (d - x)$$

$$\text{lever arm} = d - (x/3)$$

$$\text{stress in steel } f_{st} = \frac{M}{(d - \frac{x}{3})A_{st}}$$

Stress in concrete:

$$\text{From strain diagram, } \frac{\frac{f_{cb}}{E_c}}{\frac{f_{st}}{E_s}} = \frac{x}{d-x}$$

$$f_{cb} = \frac{f_{st}}{E_s/E_c} \times \frac{x}{d-x} = \frac{f_{st}}{m} \times \frac{x}{d-x}$$

$$\text{M.R in compression} = \sigma_{cbc}(bx/2)(L.A)$$

$$\text{M.R in tension} = \sigma_{st}A_{st}(L.A)$$

#### Question 4:

A rectangular beam of width 200 mm and effective depth 460 mm reinforced with 3-16 mm dia bar. The section is subjected to a characteristic moment of 30 KNm. Determine the maximum stress in steel and concrete. The materials are M20 grade concrete and mild steel reinforcement. Also find out the M.R of the section.

#### Solution :

For M20 grade concrete and Fe250

$$m = 13.33$$

$$\begin{aligned} \text{transformed area of steel} &= 13.33 \times 603 \\ &= 8038 \text{ mm}^2 \end{aligned}$$

To find neutral axis, taking moments of transformed area about N.A

$$200 \times x \times (x/2) = 8038(460 - x)$$

$$100x^2 + 8038x - 36987480 = 0$$

$$x = 156.2 \text{ mm}$$

$$\text{lever arm} = 460 - (156.2/3) = 407.9 \text{ mm}$$

$$\text{steel stress} = \frac{30 \times 10^6}{603 \times 407.9} = 121.97 \text{ N/mm}^2$$

$$\text{concrete stress} = \frac{f_{st}}{m} \times \frac{x}{d-x} = \frac{121.97}{13.33} \times \frac{156.2}{303.8} = 4.7 \text{ N/mm}^2$$

$$\text{M.R in compression} = \frac{7 \times 200 \times 156.2}{2} \times 407.9 \times 10^{-6} = 44.6 \text{ KNm}$$

$$\text{M.R in tension} = 140 \times 603 \times 407.9 \times 10^{-6} = 34.43 \text{ KNm}$$

$$\text{M.R of the section} = 34.43 \text{ KNm}$$

#### Analysis of the section:

**Type 1:** to find out the depth of neutral axis for a given section and specifying the type of beam

- If the section and steel area are given, find out neutral axis by taking moment of transformed areas about Neutral Axis.

$$b \times x \times (x/2) = m A_{st}(d-x)$$

- Find out depth of neutral axis for a balanced section.

$$x = kd \quad \text{where } k = \frac{1}{1 + \frac{\sigma_{st}}{m \sigma_{cbc}}}$$

- If  $x_{act} < x_{bal}$ , - the beam section is under reinforced.

If  $x_{act} > x_{bal}$ , - the beam section is over reinforced

If  $x_{act} = x_{bal}$ , - the beam section is balanced

**Type 2 :** to find the moment of resistance for a given section

- Find the position of actual and balanced N.A as explained above.
- If  $x_{act} < x_{bal}$ , the beam section is under reinforced and moment of resistance is given by M.R  
 $= A_{st} \sigma_{st} (d - x/3)$
- If  $x_{act} > x_{bal}$ , the beam section is over reinforced and moment of resistance is given by M.R  
 $= b \times x \times (\sigma_{cbc}/2) (d - x/3)$

**Design of the section :**

**Type – 1:** dimension not given

- The moment of resistance of balanced section  $M_{bal} = Q_{bal} b d^2$ . Out of the two variable “b” and “d”, one must known to us. It is usual to fix the width (b) of the section.
- Once width is fixed, the depth will be calculated from following formula

$$d = \sqrt{\frac{M}{Q_{bal} \times b}}$$

here  $M = M_{bal}$ , where M is the applied moment.

- Then area of steel ( $A_{st}$ ) will be calculated as per the following formula

$$A_{st} = \frac{M}{\sigma_{st} \times j d}$$

**Type 2:** dimensions are given

- Applied moment M, the section dimensions b and d are given
- Determine  $M_{bal} = Q_{bal} b d^2$
- If  $M < M_{bal}$ , the section is designed as under reinforced beam.
- If  $M > M_{bal}$ , the section is designed as over reinforced beam.
- If  $M = M_{bal}$ , the section is designed as balanced.

**Question 5:**

An R.C.C beam, 300 mm wide and 460 mm effective depth is reinforced with 4 nos. of 12 mm dia bars in tension. Find out the depth of neutral axis and type of the beam. The materials are M20 grade concrete and Fe415 grade steel.

**Solution :**

For M20 grade concrete,  $m = 13.33$

$$A_{st} = 4 \times 113 = 452 \text{ mm}^2$$

Let x be the depth of N.A

Taking moment of transformed areas about N.A

$$b \times x \times (x/2) = m A_{st} (d - x)$$

$$(300/2)x^2 = 13.33 \times 452 (460 - x)$$

$$x^2 + 40.17x - 18477 = 0$$

$$x = 117.3 \text{ mm}$$

$$\text{depth of balanced N.A} = 0.29 \times 460 = 133.4 \text{ mm}$$

$$X_{\text{actual}} < X_{\text{bal}}$$

The beam is under reinforced.

#### Question 6:

Find the M.R of a beam having width 230 mm and 560 mm effective depth reinforced with 3 nos. of 20 mm dia bar. Also state the type of the beam. The materials are M20 grade concrete and Fe415 grad steel.

#### Solution:

For M20 grade concrete,  $m = 13.33$

$$A_{st} = 3 \times 314 = 942 \text{ mm}^2$$

Let  $x$  be the depth of N.A

Taking moment of transformed areas about N.A

$$b \times x \times (x/2) = m A_{st} (d - x)$$

$$(230/2)x^2 = 13.33 \times 942(560 - x)$$

$$x^2 + 109.2x - 61146 = 0$$

$$x = 198.6 \text{ mm}$$

$$\text{depth of balanced N.A} = kd = 0.29 \times 560 = 162.4 \text{ mm}$$

$$X_{\text{actual}} > X_{\text{bal}}$$

The beam is over reinforced and concrete will fail first.

$$\begin{aligned} \text{M.R} &= b \times x \times (\sigma_{cbc}/2)(d - x/3) \\ &= 230 \times 198.6 \times (7/2)(560 - 198.6/3) \times 10^{-6} \\ &= 78.95 \text{ Knm} \end{aligned}$$

#### Question 7:

Design a reinforced concrete beam subjected to a bending moment of 20 Knm. Use M20 Grade concrete and Fe 415 grade steel. Keep the width of the beam equal to half the effective depth.

#### Solution :

For M20 grade concrete,  $m = 13.33$

$$\begin{aligned} \text{Neutral axis constant} = k &= \frac{1}{1 + \frac{\sigma_{st}}{m \sigma_{cbc}}} = \frac{1}{1 + \frac{230}{13.33 \times 7}} \\ &= 0.29 \end{aligned}$$

$$\begin{aligned} \text{Lever arm constant} = j &= \left(1 - \frac{k}{3}\right) = \left(1 - \frac{0.29}{3}\right) \\ &= 0.90 \end{aligned}$$

$$\begin{aligned} M_{\text{bal}} &= Q_{\text{bal}} b d^2 \\ &= \frac{1}{2} \sigma_{cbc} k j b d^2 = \frac{1}{2} \times 7 \times 0.29 \times 0.90 \times (d/2) \times d \\ &= 0.457 d^3 \end{aligned}$$

$$M = 20 \text{ Knm} = 20 \times 10^6 \text{ Nmm}$$

$$M_{\text{bal}} = M$$

$$0.457 d^3 = 20 \times 10^6$$

$$d = 353 \text{ mm}$$

$$b = 353/2 = 177 \text{ mm}$$

$$\text{steel area} = A_{st} = A_{stbal} = \frac{M}{\sigma_{st} j d}$$

$$A_{st} = \frac{20 \times 10^6}{230 \times 0.90 \times 353} = 273 \text{ mm}^2$$

## **PHILOSOPHY OF LIMIT STATE METHOD**

### **SAFETY AND SERVICEABILITY REQUIREMENTS**

In the method of design based on limit state concept, the structure shall be designed to withstand safely all loads liable to act on it throughout its life; it shall also satisfy the serviceability requirements, such as limitations on deflection and cracking. The acceptable limit for the safety and serviceability requirements before failure occurs is called a 'limit state'. The aim of design is to achieve acceptable probabilities that the structure will not become unfit for the use for which it is intended that it will not reach a limit state.

All relevant limit states shall be considered in design to ensure an adequate degree of safety and serviceability. In general, the structure shall be designed on the basis of the most critical limit state and shall be checked for other limit states.

For ensuring the above objective, the design should be based on characteristic values for material strengths and applied loads, which take into account the variations in the material strengths and in the loads to be supported. The characteristic values should be based on statistical data if available; where such data are not available they should be based on experience. The 'design values'

are derived from the characteristic values through the use of partial safety factors, one for material strengths and the other for loads.

### **Limit State of Collapse**

The limit state of collapse of the structure or part of the structure could be assessed from rupture of one or more critical sections and from buckling due to elastic or plastic instability (including the effects of sway where appropriate) or overturning. The resistance to bending, shear, torsion and axial loads at every section shall not be less than the appropriate value at that section produced by the probable most unfavourable combination of loads on the structure using the appropriate partial safety factors.

### **Limit State Design**

For ensuring the design objectives, the design should be based on characteristic values for material strengths and applied loads (actions), which take into account the probability of variations in the material strengths and in the loads to be supported. The characteristic values should be based on statistical data, if available. Where such data is not available, they should be based on experience. The design values are derived from the characteristic values through the use of partial safety factors, both for material strengths and for loads. In the absence of special considerations, these factors should have the values given in this section according to the material, the type of load and the limit state being considered.

Limit states are the states beyond which the structure no longer satisfies the performance requirements specified. The limit states are classified as

- a) Limit state of strength
- b) Limit state of serviceability

**a) The limit state of strength** are those associated with failures (or imminent failure), under the action of probable and most unfavorable combination of loads on the structure using the appropriate partial safety factors, which may endanger the safety of life and property. The limit state of strength includes:

- Loss of equilibrium of the structure as a whole or any of its parts or components.
- Loss of stability of the structure (including the effect of sway where appropriate and overturning) or any of its parts including supports and foundations.
- Failure by excessive deformation, rupture of the structure or any of its parts or components.
- Fracture due to fatigue.
- Brittle fracture.

**b) The limit state of serviceability** include

- Deformation and deflections, which may adversely affect the appearance or, effective, use of the structure or may cause improper functioning of equipment or services or may cause damages to finishes and non-structural members.
- Vibrations in the structure or any of its components causing discomfort to people, damages to the structure, its contents or which may limit its functional effectiveness. Special consideration shall be given to floor vibration systems susceptible to vibration, such as large open floor areas free of partitions to ensure that such vibrations is acceptable for the intended use and occupancy.
- Repairable damage due to fatigue.
- Corrosion and durability.

### **Limit States of Serviceability**

To satisfy the limit state of serviceability the deflection and cracking in the structure shall not be excessive. This limit state corresponds to deflection and cracking.

#### **Deflection**

The deflection of a structure or part shall not adversely affect the appearance or efficiency of the structure or finishes or partitions.

#### **Cracking**

Cracking of concrete should not adversely affect the appearance or durability of the structure; the acceptable limits of cracking would vary with the type of structure and environment. The actual width of cracks will vary between the wide limits and predictions of absolute maximum width are

not possible. The surface width of cracks should not exceed 0.3mm.

In members where cracking in the tensile zone is harmful either because they are exposed to the effects of the weather or continuously exposed to moisture or in contact soil or ground water, an upper limit of 0.2 mm is suggested for the maximum width of cracks. For particularly aggressive environment, such as the 'severe' category, the assessed surface width of cracks should not in general, exceed 0.1 mm.

## **CHARACTERISTIC AND DESIGN VALUES AND PARTIAL SAFETY FACTORS**

### **1. Characteristic Strength of Materials**

Characteristic strength means that value of the strength of the material below which not more than 5 percent of the test results are expected to fall and is denoted by  $f_{ck}$ . The characteristic strength of concrete ( $f_{ck}$ ) is as per the mix of concrete. The characteristic strength of steel ( $f_y$ ) is the minimum stress or 0.2 percent of proof stress.

### **2. Characteristic Loads**

Characteristic load means that value of load which has a 95 percent probability of not being exceeded during the life of the structure. Since data are not available to express loads in statistical terms, for the purpose of this standard, dead loads given in IS 875 (Part 1), imposed loads given in IS 875 (Part 2), wind loads given in IS 875 (Part 3), snow load as given in IS 875 (Part 4) and seismic forces given in IS 1893-2002(part-I) shall be assumed as the characteristic loads.





**Design values:****Material:**

The design strength of material  $f_d$  is given by

$$f_d = \frac{f}{\gamma_m}$$

where  $f$  = characteristic strength of materials

$\gamma_m$  = partial safety factor appropriate to the material

**Loads:**

The design load  $F_d$  is given by

$$F_d = F \gamma_f$$

Where  $F$  = characteristic load

$\gamma_f$  = partial safety factor appropriate to the nature of loading

**Partial Safety Factors:****1. Partial Safety Factor  $\gamma_f$  for Loads**

Sr. No.	Load Combination	Ultimate Limit State	Serviceability Limit State
1	DL + LL	1.5 (DL + LL)	DL + LL
2	DL + WL i) DL contribute to stability ii) DL assists overturning	0.9 DL + 1.5 WL 1.5 (DL + WL)	DL + WL DL + WL
3	DL + LL + WL	1.2 (DL + LL + WL)	DL + 0.8 LL + 0.8 WL

**2. Partial Safety Factor  $\gamma_m$  for Material Strength**

Sr. No.	Material	Ultimate Limit State	Serviceability Limit State
1	Concrete	1.50	$E_c = 5000 \sqrt{f_{ck}} \text{ MPa}$
2	Steel	1.15	$E_s = 2 \times 10^5 \text{ MPa}$

When assessing the strength of a structure or structural member for the limit state of collapse, the values of partial safety factor, should be taken as 1.5 for concrete and 1.15 for steel.


# ANALYSIS AND DESIGN OF SINGLE AND DOUBLE REINFORCED SECTION

## LIMIT STATE OF COLLAPSE: FLEXURE


### Assumptions for Limit State of Collapse (Flexure):

- 1) Plane section normal to the axis remains plane even after bending. i.e. strain at any point on the cross section is directly proportional to the distance from the N.A.
- 2) Maximum strain in concrete at the outer most compression fibre is taken as 0.0035 in bending.
- 3) The relationship between the compressive stress distribution in concrete and the strain in concrete may be assumed to be rectangle, trapezoid, parabola or any other shape which results in prediction of strength in substantial agreement with the results of test. An acceptable stress strain curve is shown below

For design purposes, the compressive strength of concrete in the structure shall be assumed to be

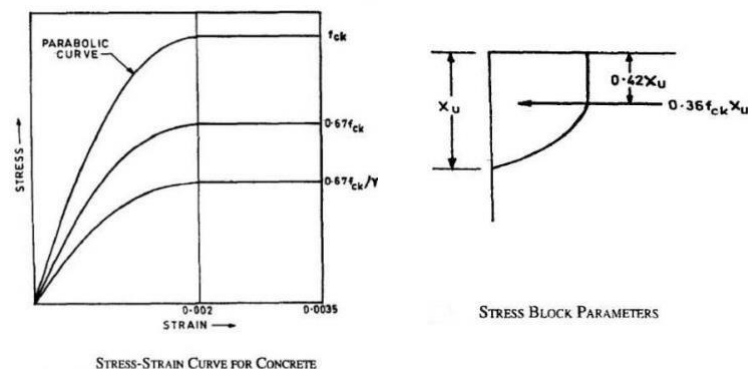

0.67 times the characteristic strength. The partial safety factor  $\gamma_m = 1.5$  shall be applied in addition to this.

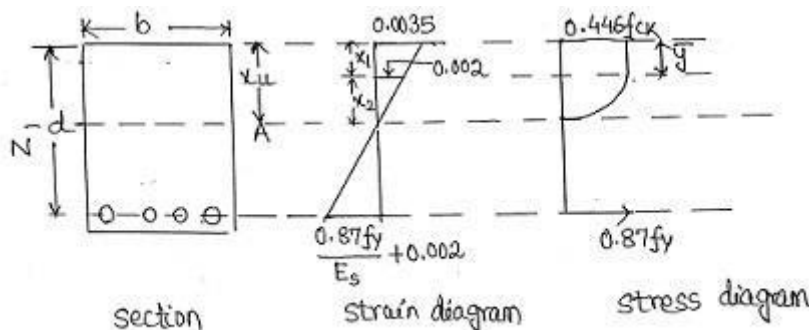

NOTE –

For the above stress-strain curve the design stress block parameters are as follows:

$$\begin{aligned}\text{Area of parabolic portion} &= (2/3) \times 0.446 f_{ck} \times (4/7) x_u \\ &= 0.17 f_{ck} x_u\end{aligned}$$

$$\begin{aligned}\text{Area of rectangular portion} &= 0.446 f_{ck} (3/7) x_u \\ &= 0.19 f_{ck} x_u\end{aligned}$$

$$\text{Total area of stress block} = 0.17 f_{ck} x_u + 0.19 f_{ck} x_u = 0.36 f_{ck} x_u$$

Let  $\bar{y}$  be the distance of centroid of stress block from the extreme compression fibre

$$\bar{y} = \frac{0.17 f_{ck} x_u (x_1 + \frac{3}{8} x_2) + 0.19 f_{ck} x_u (\frac{x_1}{2})}{0.36 f_{ck} x_u}$$


substituting  $x_1 = (3/7) x_u$

$$x_2 = (4/7) x_u$$

Depth of centre of compressive force =  $\bar{y} = 0.42 x_u$  from the extreme fibre in compression

Where  $f_{ck}$  = characteristic compressive strength of concrete, and  $x_u$  = depth of neutral axis

- 4) the tensile strength of the concrete is ignored.
- 5) the stresses in the reinforcement are derived from representative stress – strain curve for the type of steel used.

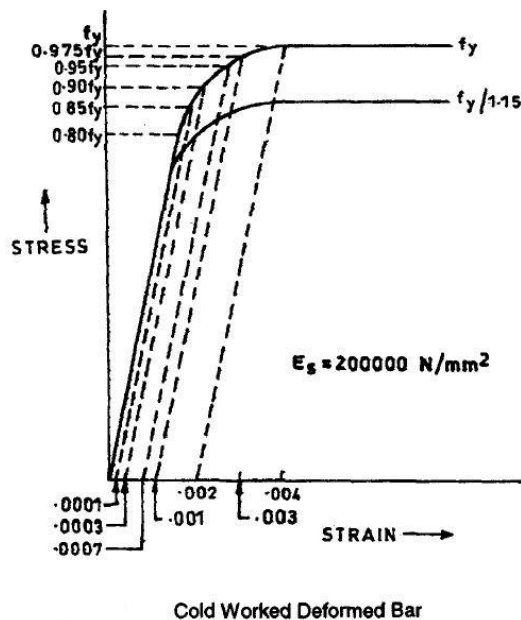

- 6) the maximum strain in tension reinforcement in the section at failure shall not be less than  


$$= \frac{0.87 f_y}{E_s} + 0.002$$

### TYPES OF BEAM SECTIONS

- Section in which, tension steel reaches yield strain simultaneously as the concrete reaches the failure strain in bending are called, '**Balanced Section**'.
- Section in which, tension steel reaches yield strain at loads lower than the load at which concrete reaches the failure strain in bending are called, '**Under Reinforced Section**'
- Section in which, tension steel reaches yield strain at loads higher than the load at which concrete reaches the failure strain in bending are called, '**Over Reinforced Section**'.

**Analysis of single reinforced rectangular beam :**

**Derivation of formula:**

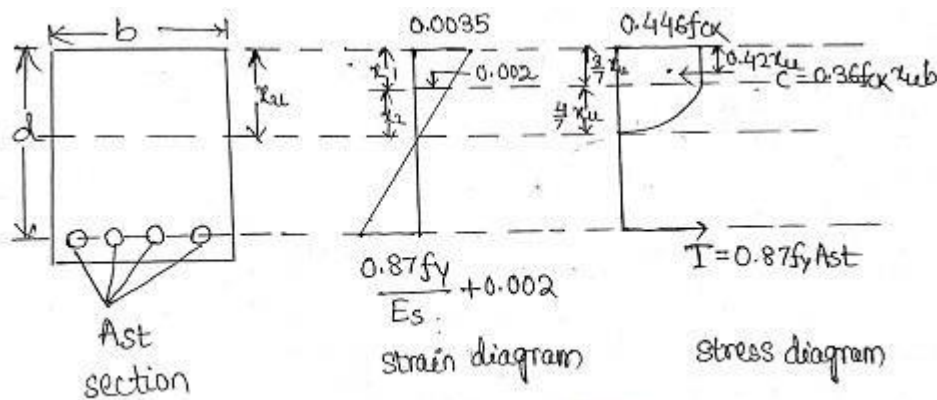

A singly reinforced rectangular beam section with strain diagram and stress diagram are shown in figure.

**To find Neutral axis:**

Total compression = total tension

$$0.36 f_{ck} b x_u = 0.87 f_y A_{st}$$

$$x_u = \frac{0.87 f_y A_{st}}{0.36 f_{ck} b}$$

- If  $x_u < x_{u_{max}}$ , the section is under reinforced section
- If  $x_u > x_{u_{max}}$ , the section is over reinforced section, then  $x_u = x_{u_{max}}$
- If  $x_u = x_{u_{max}}$ , the section is balanced section

Grade of steel	$x_{u\max}/d$
Fe250	0.53
Fe415	0.48
Fe500	0.46

**To find lever arm:**

From the stress diagram, the lever arm

$$Z = d - 0.42 x_u$$

**To find moment of resistance:**

(1) For a balanced section

$$M.R = \text{total compression} \times \text{lever arm}$$

$$= \text{total tension} \times \text{lever arm}$$

$$M_u = 0.36 f_{ck} b x_u (d - 0.42 x_u)$$

For limiting value substitute  $x_{u\max}$  for  $x_u$  and  $M_{u\lim}$  for  $M_u$

$$M_{u\lim} = 0.36 \left( \frac{x_{u\max}}{d} \right) \left( 1 - 0.42 \frac{x_{u\max}}{d} \right) f_{ck} b d^2$$

$$= Q_{\lim} b d^2$$

$Q_{\lim}$  = limiting moment of resistance factor for balanced rectangular section.

For under reinforced section

$$M_u = 0.87 f_y A_{st} (d - 0.42 x_u)$$

$$= 0.87 f_y A_{st} d \left( 1 - \frac{f_y A_{st}}{b d f_{ck}} \right)$$

**Type of problem:**

Three different types of problems are considered for singly reinforced rectangular beams

**Type 1:**

To find out the depth of neutral axis and specifying the type of the beam

- For a given section, equate total tension and total compression and thus find out the depth of neutral axis using

$$X_u = \frac{0.87 f_y A_{st}}{0.36 f_{ck} b}$$

- Also find out the limiting value of depth of neutral axis  $x_{u\max}$ , using  $x_{u\max}/d$
- Then if

If  $x_u < x_{u\max}$ , the section is under reinforced section

If  $x_u > x_{u\max}$ , the section is over reinforced section, then  $x_u = x_{u\max}$

If  $x_u = x_{u\max}$ , the section is balanced section

### Type 2:

To find out moment of resistance of a given section

- Find out depth of neutral axis and type of the beam as discussed in type 1
- For over reinforced and balanced section, obtain moment of resistance by using the following equation

$$M_{ulim} = 0.36 \left( \frac{x_{umax}}{d} \right) \left( 1 - 0.42 \frac{x_{umax}}{d} \right) f_{ck} b d^2$$

- For under reinforced section obtain moment of resistance by using the following equation

$$M_u = 0.36 f_{ck} b x_u (d - 0.42 x_u)$$

Or

$$M_u = 0.87 f_y A_{st} (d - 0.42 x_u)$$

### Type 3:

To design a singly reinforced rectangular section for given width and applied factored moment

The width is usually decided by the functional or architectural requirement.

$$d = \sqrt{\frac{M}{Q_{lim} \times b}}$$

The steel area can be obtained by using the following formula

$$A_{st} = \frac{M_u}{0.87 f_y (d - 0.42 x_{umax})}$$

### Question 1:

A rectangular beam 230 mm wide and 520 mm effective depth is reinforced with 4 nos. of 16 mm diameter bars. Find out the depth of neutral axis and specify the type of beam. The materials are M20 grade concrete and Fe415 grade steel. Also find out the depth of neutral axis if the reinforcement is increased to 4 nos. of 20 mm dia bars.

**Solution:**

#### Case 1:

$$A_{st} = 4 \times 201 = 804 \text{ mm}^2$$

$$\text{Total compression} = 0.36 f_{ck} b x_u = 0.36 \times 20 \times 230 x_u = 1656 x_u$$

$$\text{Total tension} = 0.87 f_y A_{st} = 0.87 \times 415 \times 804 = 290284$$

Equating total compression = total tension

$$1656 x_u = 290284$$

$$x_u = 175.3 \text{ mm}$$

$$\text{limiting value of neutral axis} = x_{umax} = 0.48d = 0.48 \times 520 = 250 \text{ mm}$$

here  $x_u < x_{umax}$ , the section is under reinforced section

#### Case 2 :

$$x_u = 175.3 \text{ mm}$$

$$A_{st} = 4 \times 314 = 1256 \text{ mm}^2$$

$$\text{Total compression} = 0.36 f_{ck} b x_u = 0.36 \times 20 \times 230 x_u = 1656 x_u$$

$$\text{Total tension} = 0.87 f_y A_{st} = 0.87 \times 415 \times 1256 = 453479$$

$$1656 x_u = 453479$$

$$x_u = 273.8 \text{ mm}$$

Here  $x_u > x_{u\max}$ , the section is over reinforced section

$$x_u = x_{u\max} = 250 \text{ mm}$$

### Question 2:

A rectangular beam 230 mm wide and 460 mm effective depth is reinforced with 3 nos. of 20 mm diameter bars. Find out the factored moment of resistance of the beam. The materials are M20 grade concrete and Fe415 grade steel. Also find out the factored moment of resistance if the reinforcement is increased to 5 nos. of 20 mm dia bars.

**Solution:**

$$A_{st} = 3 \times 314 = 942 \text{ mm}^2$$

$$\text{Total compression} = 0.36 f_{ck} b x_u = 0.36 \times 20 \times 230 x_u = 1656 x_u$$

$$\text{Total tension} = 0.87 f_y A_{st} = 0.87 \times 415 \times 942 = 340109$$

Equating total compression = total tension

$$1656 x_u = 340109$$

$$x_u = 205.4 \text{ mm}$$

$$\text{limiting value of neutral axis} = x_{u\max} = 0.48d = 0.48 \times 460 = 220.8 \text{ mm}$$

Here  $x_u < x_{u\max}$ , the section is under reinforced section

$$\begin{aligned} M_u &= 0.36 f_{ck} b x_u (d - 0.42 x_u) \\ &= 0.36 \times 20 \times 230 \times 205.4 (460 - 0.42 \times 205.4) = 127.12 \times 10^6 = 127 \text{ KNm} \end{aligned}$$

### Case 2 :

$$A_{st} = 4 \times 314 = 1256 \text{ mm}^2$$

$$\text{Total compression} = 0.36 f_{ck} b x_u = 0.36 \times 20 \times 230 x_u = 1656 x_u$$

$$\text{Total tension} = 0.87 f_y A_{st} = 0.87 \times 415 \times 1256 = 453479$$

$$1656 x_u = 453479$$

$$x_u = 273.8 \text{ mm}$$

$$x_{u\max} = 0.48d = 0.48 \times 460 = 220.8 \text{ mm}$$

here  $x_u > x_{u\max}$ , the section is over reinforced section

$$x_u = x_{u\max} = 220.8 \text{ mm}$$

$$M_u = 0.36 f_{ck} b x_u (d - 0.42 x_u)$$

$$= 0.36 \times 20 \times 230 \times 220.8 (460 - 0.42 \times 220.8) = 134.2 \times 10^6 = 134 \text{ Knm}$$

### Question 3:

Design a singly reinforced rectangular beam for an applied factored moment of 120 Knm.

Assume the width of section as 230 mm. The materials are M20 grade concrete and Fe415 grade steel

### Solution:

$$M_u = 120 \text{ Knm}$$

$$b = 230 \text{ mm}$$

$$f_{ck} = 20 \text{ N/mm}^2$$

$$f_y = 415 \text{ N/mm}^2$$

$$d = \sqrt{\frac{M}{Q_{lim} \times b}} = \sqrt{\frac{120 \times 10^6}{2.76 \times 230}} = 434.8 \text{ mm}$$

adopt  $D = 500 \text{ mm}$

$$d = 500 - 30 - (20/2) = 460 \text{ mm}$$

$$A_{st} = \frac{M_u}{0.87 f_y (d - 0.42 x_{u\max})} = \frac{120 \times 10^6}{0.87 \times 415 (460 - 0.42 \times 0.48 \times 460)}$$



$$A_{st} = 904.97 \text{ mm}^2$$

### Doubly reinforced beam:

If the applied moment is greater than the M.R of a singly reinforced section, there can be three alternatives

- (a) If possible increase the dimension of the section preferably depth
- (b) Higher grade concrete can be used to increase the M.R of the section
- (c) Steel reinforcement may be added in compression zone to increase the M.R of the section. This is known as doubly reinforced section.

**Derivation of the formula:**

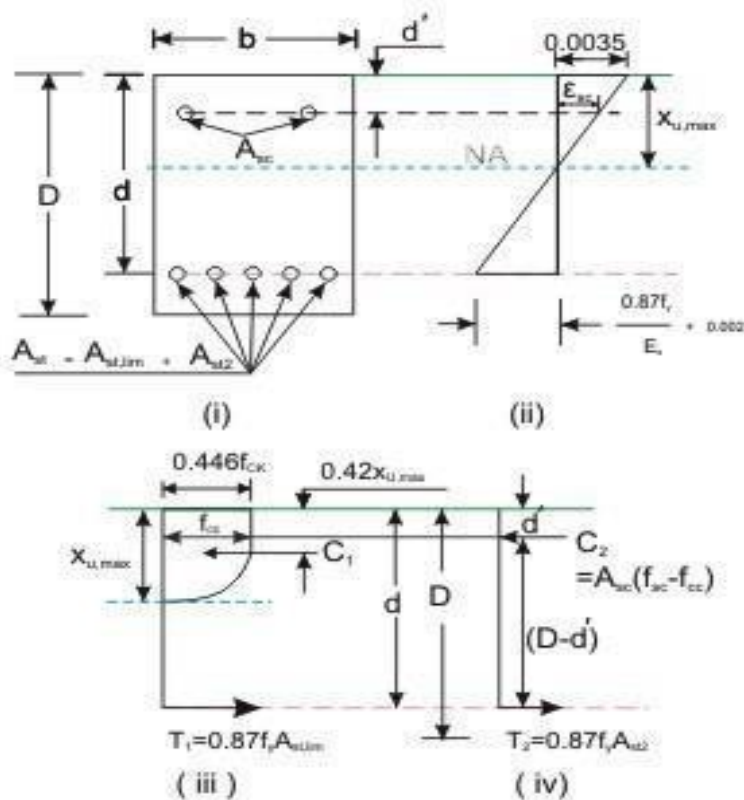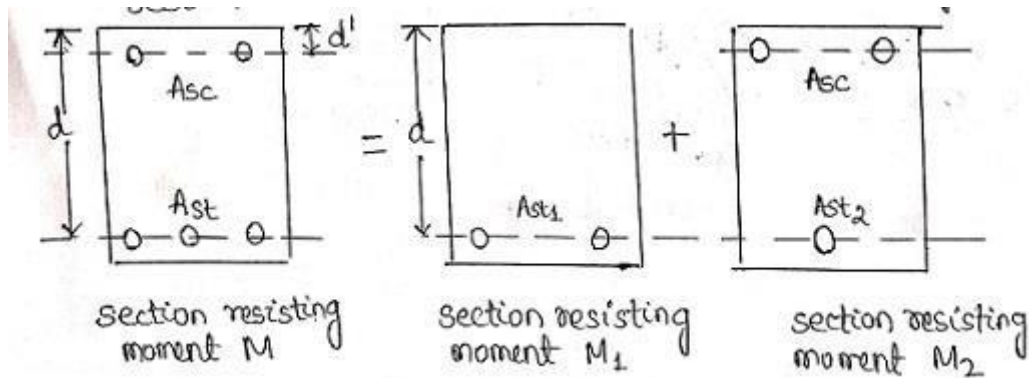

- (i) Beam cross section
- (ii) Strain diagram
- (iii) Force diagram of beam of  $M_{u,lim}$
- (iv) Force diagram of beam of  $M_{u2}$

A doubly reinforced beam subjected to a moment  $M_u$  can be expressed as a rectangular section with tension reinforcement  $A_{st,lim}$  reinforced for balanced condition giving moment of resistance  $M_{u,lim}$  + an auxiliary section reinforced with compression reinforcement  $A_{sc}$  and tensile reinforcement  $A_{st2}$  giving moment of resistance  $M_{u2}$  such that

$$M_u = M_{u,lim} + M_{u2}$$

For the moment  $M_{u\lim}$  the tension steel  $A_{st\lim}$  is found out as explained for singly reinforced beams.

For the additional moment  $M_{u2}$ , the additional tension steel and compression steel are provided such that they give a couple of moment  $M_{u2}$

Let the compression reinforcement be provided at a depth  $d'$  from the extreme compression fibre. Then lever arm for additional moment will be  $(d - d')$

Considering tension steel

$$M_{u2} = 0.87 f_y A_{st2} (d - d')$$

Considering compression steel

$$M_{u2} = A_{sc} (f_{sc} - f_{cc}) (d - d')$$

Where,  $A_{st2}$  = Area of additional tensile reinforcement

$A_{sc}$  = Area of compression reinforcement

$f_{sc}$  = Stress in compression reinforcement

$f_{cc}$  = Compressive stress in concrete at the level of compression reinforcement

Since the additional reinforcement is balanced by the additional compressive force.

$$A_{sc} (f_{sc} - f_{cc}) = 0.87 f_y A_{st2}$$

$$A_{st2} = \frac{A_{sc} (f_{sc} - f_{cc})}{0.87 f_y}$$

Total area of reinforcement shall be obtained by

$$A_{st} = A_{st1} + A_{st2}$$

$A_{st1}$  = Area of reinforcement for a singly reinforced section for  $M_{u\lim}$

The value of  $f_{sc}$  in  $N/mm^2$  can be obtained from the following table for different values of  $d/d'$  and grade of steel

fy in $N/mm^2$	d/d'			
	0.05	0.1	0.15	0.20
250	217	217	217	217
415	355	353	342	329
500	424	412	395	370
550	458	441	419	380

Note : The value of  $f_{cc}$  is very small as compared to the value of  $f_{sc}$  and can be neglected.

**Type of problem :**

**Type 1: To find out the moment of resistance of a given section**

Total compression = total tension

$$C_1 + C_2 = T$$

$$0.36f_{ck}bx_u + A_{sc}(f_{sc}) = 0.87 f_y A_{st}$$

Find out  $x_u$

Find  $x_{u\max}$  and type of beam

If  $x_u > x_{u\max}$ , the section is over reinforced section, then  $x_u = x_{u\max}$

$$M_u = 0.36 f_{ck} b x_u (d - 0.42 x_u) + A_{sc}(f_{sc})(d - d')$$

**Type 2: To find out reinforcement for flexure for a given section and factored moment**

Find out  $M_{ulim}$  and reinforcement  $A_{stlim}$  for a given section by using the following equation

$$M_{ulim} = 0.36 f_{ck} b x_{u\max} (d - 0.42 x_{u\max})$$

$$A_{stlim} = \frac{M_{ulim}}{0.87 f_y (d - 0.42 x_{u\max})}$$

Obtain  $M_{u2} = M_u - M_{ulim}$

Find compression steel from following equation

$$M_{u2} = A_{sc}(f_{sc})(d - d')$$

$$A_{sc} = \frac{M_{u2}}{f_{sc}(d - d')}$$

Corresponding tension steel can be found out by from

$$A_{st2} = \frac{A_{sc}(f_{sc} - f_{cc})}{0.87 f_y}$$

$$A_{st} = A_{stlim} + A_{st2}$$

**Question 1:**

Find the factored moment of resistance of a beam section 230 mm wide and 460 mm effective depth reinforced with 2 nos. of 16 mm dia bars as compression reinforcement at an effective cover of 40 mm and 4 nos. of 20 mm dia bars as tension reinforcement. The materials are M20 grade concrete and Fe250 grade steel.

**Solution:**

$$b = 230 \text{ mm}$$

$$d = 460 \text{ mm}$$

$$f_{ck} = 20 \text{ N/mm}^2$$

$$f_y = 250 \text{ N/mm}^2$$

$$d' = 40 \text{ mm}$$

$$A_{sc} = 2 \times 201 = 402 \text{ mm}^2$$

$$A_{st} = 4 \times 314 = 1256 \text{ mm}^2$$

$$C_1 + C_2 = T$$

$$0.36f_{ck}bx_u + A_{sc}(f_{sc}) = 0.87 f_y A_{st}$$

For  $d'/d = 40/460 = 0.08$ , next higher value 0.1 may be adopted

$$f_{sc} = 217 \text{ N/mm}^2$$

$$0.36 \times 20 \times 230 x_u + 402 \times 217 = 0.87 \times 250 \times 1256$$

$$1656 x_u = 273180 - 87234 = 185946$$

$$x_u = 112.29 \text{ mm}$$

$$x_{u\max} = 0.53d = 0.53 \times 460 = 243.8 \text{ mm}$$

$x_u < x_{u\max}$ , the section is under reinforced section

$$x_u = 112.29 \text{ mm}$$

$$\begin{aligned} M_u &= 0.36 f_{ck} b x_u (d - 0.42 x_u) + A_{sc} (f_{sc}) (d - d') \\ &= 0.36 \times 20 \times 230 \times 112.29 (460 - 0.42 \times 112.29) + 402 \times 217 (460 - 40) \\ &= 76.76 + 36.64 = 113.4 \text{ Knm} \end{aligned}$$

### Question 2:

A rectangular beam of size 230 mm wide and 500 mm depth is subjected to a factored moment of 200 Knm. Find the reinforcement for flexure. The materials are M20 grade concrete and Fe415 grade steel.

### Solution:

$$M_u = 200 \text{ Knm}$$

$$\begin{aligned} M_{ulim} &= 0.36 f_{ck} b x_{u\max} (d - 0.42 x_{u\max}) \\ &= 0.36 \times 20 \times 230 \times 0.48 \times 500 (500 - 0.42 \times 0.48 \times 500) = 158.7 \text{ Knm} \end{aligned}$$

$$d' = 50 \text{ mm}$$

$$d'/d = 50/500 = 0.1$$

$$f_{sc} = 353 \text{ N/mm}^2$$

$$M_{u2} = M_u - M_{ulim} = 200 - 158.7 = 41.3 \text{ Knm}$$

$$A_{sc} = \frac{M_{u2}}{f_{sc} (d - d')} = \frac{41.3 \times 10^6}{353 (500 - 50)} = 260 \text{ mm}^2$$

$$A_{st2} = \frac{A_{sc} (f_{sc} - f_{cc})}{0.87 f_y} = \frac{260 \times 353}{0.87 \times 415} = 254.2 \text{ mm}^2$$

$$A_{stim} = \frac{M_{lim}}{0.87 f_y (d - 0.42 x_{u\max})} = \frac{158.7 \times 10^6}{0.87 \times 415 (500 - 0.42 \times 0.48 \times 500)} = 1101 \text{ mm}^2$$

$$A_{st} = 1101 + 254 = 1355 \text{ mm}^2$$

## ANALYSIS AND DESIGN OF T - BEAM

### Introduction:

When there is a reinforced concrete slab over a reinforced concrete beam, the slab and beam can be designed and constructed in such a way that they can act together.


The concrete in the slab, which is on the compression side of the beam (in the middle portion of continuous beam) can be made to resist the compression force and the tension can be carried by the steel in the tension side of the beam. These combined beam and slab units are called “flanged beam”.

They may be T or L beams depending on whether the slab is on both or only on one side of the beam.

T or L beams act as flanged beams only between the supports where the bending moment is positive and the slabs are on the compression side of the beam.

Over the support where the bending moment are negative the slabs are on the tension side then the beam acts only as a rectangular beam with tension steel placed in the slab portion of the beam. Thus at places of negative moment these beams have to be designed as singly or doubly reinforced rectangular beam.

A ‘T’ beam or ‘L’ beam can be considered as a rectangular beam with dimensions  $b_w$ ,  $D$  plus a flange of size  $(b_f - b_w) \times D_f$ . It is shown in the figure beam (a) is equivalent to beam (b) + beam (c).

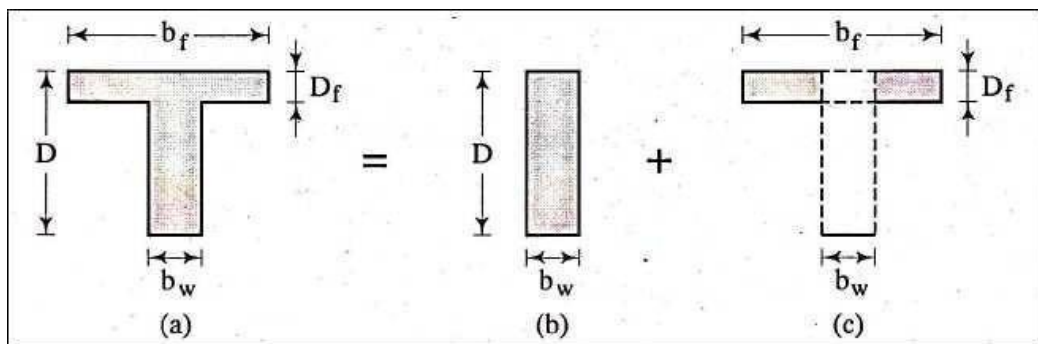

The flanged beam analysis and design are analogous to doubly reinforced rectangular beam. In doubly reinforced beams additional compressive is provided by adding reinforcement in compression zone, whereas in flanged beams, this is provided by the slab concrete, where the spanning of the slab is perpendicular to that of beam and slab is in compression zone.

If the spanning of the slab is parallel to that of the beam, some portion of slab can be made to span in the direction perpendicular to that of the beam by adding some reinforcement in the slab.


A flanged beam can be also doubly reinforced.

The moment of resistance of a T beam is sum of the moment of resistance of beam (a) is the sum moment of resistance of beam (b) and moment of resistance of beam (c). similarly the steel area required for beam (a) shall be equal to the sum of the steel required for the beam (b) and the steel area required for beam (c).

### Position of neutral axis:

For a flanged beam, the Neutral Axis either (a) lies in flange or (b) lies in web.

(a) **Neutral axis lies in flange ( $x_u < D_f$ )**

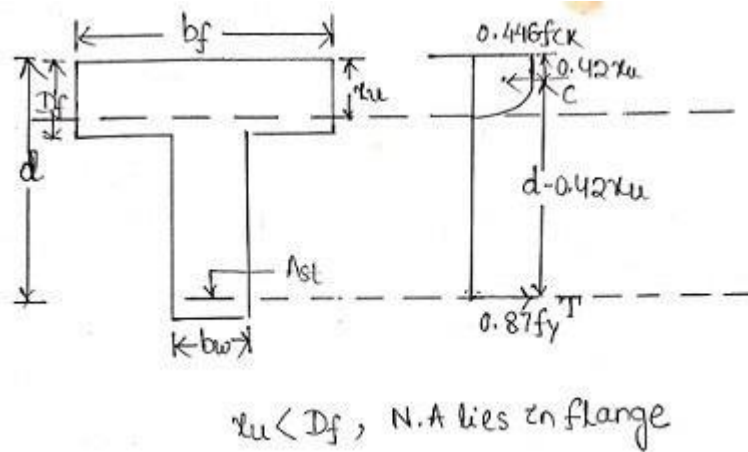

When the neutral axis lies in the flange, the size of the compression zone becomes  $b_f \times x_u$

As concrete does not resist any tension, the width of tension zone has no effect on the M.R of the section.

Therefore this beam can be considered as a rectangular beam of dimension  $b_f \times d$  and the formula derived for rectangular beams shall be applied.

For a singly reinforced rectangular beam:

Equating total compression and total tension

$$x_u = \frac{0.87 f_y A_{st}}{0.36 f_{ck} b}$$

To find out the type of the beam,  $x_{u\max}$  shall be found out and compared with actual value of neutral axis  $x_u$

If  $x_u < x_{u\max}$ , the section is under reinforced section

If  $x_u > x_{u\max}$ , the section is over reinforced section, then  $x_u = x_{u\max}$

If  $x_u = x_{u\max}$ , the section is balanced section

- For under reinforced section

$$M_u = 0.36 f_{ck} b_f x_u (d - 0.42 x_u)$$


Or

$$M_u = 0.87 f_y A_{st} (d - 0.42 x_u)$$

- For over reinforced section

$$M_{u\lim} = 0.36 f_{ck} b_f x_{u\max} (d - 0.42 x_{u\max})$$

**(b) Neutral axis lies in web ( $x_u > D_f$ )**

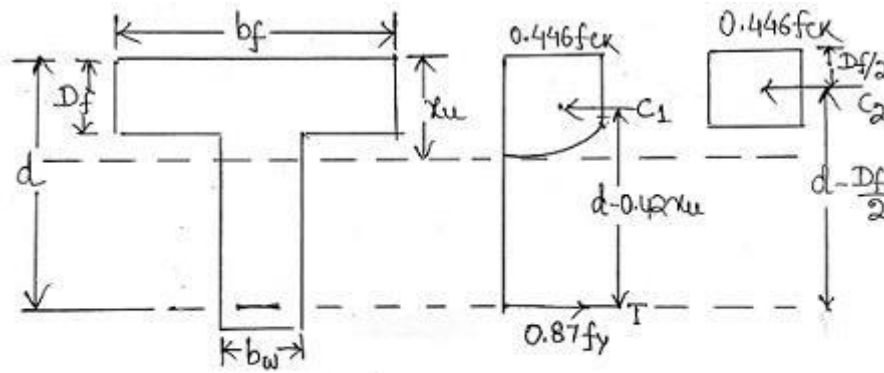

$x_u > D_f$ , N.A lies in web.

The stress block in concrete shows that the stress is uniform upto  $(3/7) x_u$  and then parabolic

**Case I:  $D_f \leq (3/7)x_u$**

In this case the stresses are uniform in flange.

$$\text{Total tension} = 0.87f_y A_{st}$$

$$\text{Total compression} = 0.36f_{ck}b_w x_u + 0.446f_{ck}(b_f - b_w)D_f$$

$$\text{Moment of resistance } M_u = 0.36f_{ck}b_w x_u(d - 0.42x_u) + 0.446f_{ck}(b_f - b_w)D_f(d - D_f/2)$$

**Case II:  $D_f > (3/7)x_u$**

The rectangular stress block in this case is assumed to be equal to  $y_f$

$$\text{Total tension} = 0.87f_y A_{st}$$

$$\text{Total compression} = 0.36f_{ck}b_w x_u + 0.446f_{ck}(b_f - b_w)y_f$$

$$\text{Moment of resistance } M_u = 0.36f_{ck}b_w x_u(d - 0.42x_u) + 0.446f_{ck}(b_f - b_w)y_f(d - y_f/2)$$

$$\text{Where } y_f = 0.15x_u + 0.65D_f$$

**Problem 1:**

A tee beam of effective flange width 1200 mm, thickness of slab 100 mm, width of rib 300 mm and effective depth of 560 mm is reinforced with 4 nos. of 25 mm dia bars. Calculate the factored moment of resistance. The materials are M<sub>20</sub> grade concrete and Fe415 grade steel.

**Solution :**

$$b_f = 1200 \text{ mm}$$

$$D_f = 100 \text{ mm}$$

$$b_w = 300 \text{ mm}$$

$$d = 560 \text{ mm}$$

$$A_{st} = 1964 \text{ mm}^2$$

Assume that N.A lies in flange ( $x_u < D_f$ )

$$\text{Total compression} = 0.36 f_{ck} b_f x_u$$

$$\text{Total tension} = 0.87f_y A_{st}$$

Equating, total compression = total tension

$$0.36 f_{ck} b_f x_u = 0.87 f_y A_{st}$$

$$0.36 \times 20 \times 1200 x_u = 0.87 \times 415 \times 1964$$

$$x_u = 82.07 \text{ mm} < D_f$$

hence N.A lies in the flange.

$$x_{u\max} = 0.48 \times 560 = 268.8 \text{ mm}$$

$x_u < x_{u\max}$ , the section is under reinforced section

$$M_u = 0.36 f_{ck} b_f x_u (d - 0.42 x_u)$$

$$= 0.36 \times 20 \times 1200 \times 82.07 (560 - 0.42 \times 82.07) = 372.65 \times 10^6 \text{ Nm}$$

$$= 372.65 \text{ Knm}$$

## **SHEAR STRESS IN REINFORCED CONCRETE BEAMS**


When a beam is loaded with transverse loads the Bending Moment (BM) varies from section to section. Shearing stresses in beams are caused by this variation of BM in the beam span. Due to the variation of BM at two sections distance  $dx$  apart, there are unequal bending stresses at the same fibre. This inequality of bending stresses produces a tendency in each horizontal fibre to slide over adjacent horizontal fibre causing horizontal shear stress, which is accompanied by complimentary shear stress in vertical direction.

### **SHEAR CRACKS IN BEAMS:-**

Under the transverse loading, at any section of the beam, there exists both Bending Moment (BM) and Shear Force (V). Depending upon the ratio of Bending Moment (BM) to Shear Force (V) at different sections, there may be three regions of shear cracks in the beam as follows.

- (a) Region I : Region of flexure Cracks.
- (b) Region II : Region of flexure shear Cracks.

(c) Region III: Region of web shear Cracks or diagonal tension cracks.

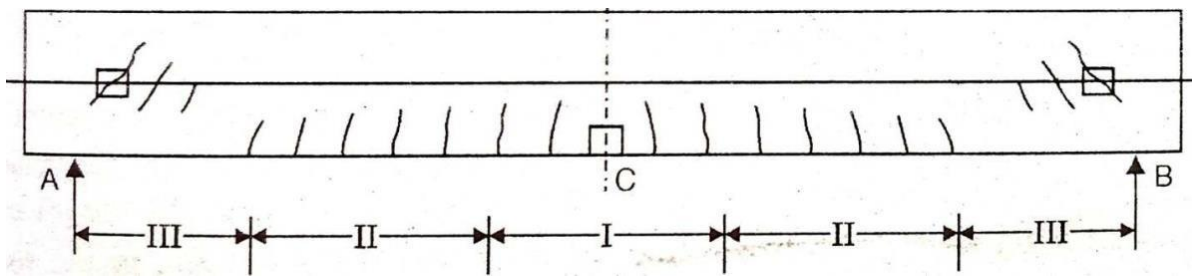

DIFFERENT REGION OF CRACKS IN BEAMS

**(a) Region I : Region of flexure Cracks.**

This region normally occurs adjacent to mid-span where BM is large and shear force is either zero or very small. The principal planes are perpendicular to beam axis. When the principal tensile stress reaches the tensile strength of the concrete (which is quite low) tensile cracks develop vertically. The cracks are known as flexural cracks resulting primarily due to flexure.

**(b) Region II: Region of flexure shear Cracks.**

These regions are near the quarter span, to both the sides, where BM is considerable and at the same time Shear force is significant. The cracks in this region are initiated at the tension face, travel vertically (due to flexure) and gradually tend to develop in the inclined direction towards the Neutral Axis (N.A.), as the shear stress goes on increasing towards the N.A. Since the cracks develop under the combined action of BM and Shear, these cracks are known as flexure-shear cracks.

**(c) Region III : Region of web shear Cracks or diagonal tension cracks.**

This region is adjacent to each support of the beam where S.F is predominant. Since Shear stress is maximum at the N.A., inclined cracks start developing at the N.A. along the diagonal of an element subject to the action of pure shear. Hence these cracks are known as diagonal tension cracks or web-shear cracks.

**Design Shear Strength of Reinforced Concrete**

Recent laboratory experiments confirmed that reinforced concrete in beams has shear strength even without any shear reinforcement. This shear strength ( $\tau_c$ ) depends on the grade of concrete and the percentage of tension steel in beams. On the other hand, the shear strength of reinforced concrete with the reinforcement is restricted to some maximum value ( $\tau_{cmax}$ ) depending on the grade of concrete. These minimum and maximum shear strengths of reinforced concrete (IS 456, cls. 40.2.1 and 40.2.3, respectively) are given below:

### Design shear strength without shear reinforcement (IS 456, cl. 40.2.1)

Table 19 of IS 456 stipulates the design shear strength of concrete  $\tau_c$  for different grades of concrete with a wide range of percentages of positive tensile steel reinforcement. It is worth mentioning that the reinforced concrete beams must be provided with the minimum shear reinforcement as per cl. 40.3 even when  $\tau_v$  is less than  $\tau_c$  given in Table 3

100A <sub>s</sub> /bd	Concrete grade		
	M20	M25	M30
≤ 0.15	0.28	0.29	0.29
0.25	0.36	0.36	0.37
0.50	0.48	0.49	0.50
0.75	0.56	0.57	0.59
1.00	0.62	0.64	0.66
1.25	0.67	0.70	0.71
1.50	0.72	0.74	0.76


### Maximum shear stress with shear reinforcement (cls. 40.2.3, 40.5.1 and 41.3.1)

Table 20 of IS 456 stipulates the maximum shear stress  $\tau_{cmax}$  of reinforced concrete in beams  $\tau_{cmax}$  as given below in Table . Under no circumstances, the nominal shear stress in beams  $\tau_v$  shall exceed  $\tau_{cmax}$  given in Table for different grades of concrete.

Maximum shear stress  $\tau_{cmax}$  N/mm<sup>2</sup>

Concrete grade	M20	M25	M30
$\tau_{cmax}$	2.8	3.1	3.5

### Critical Section for Shear

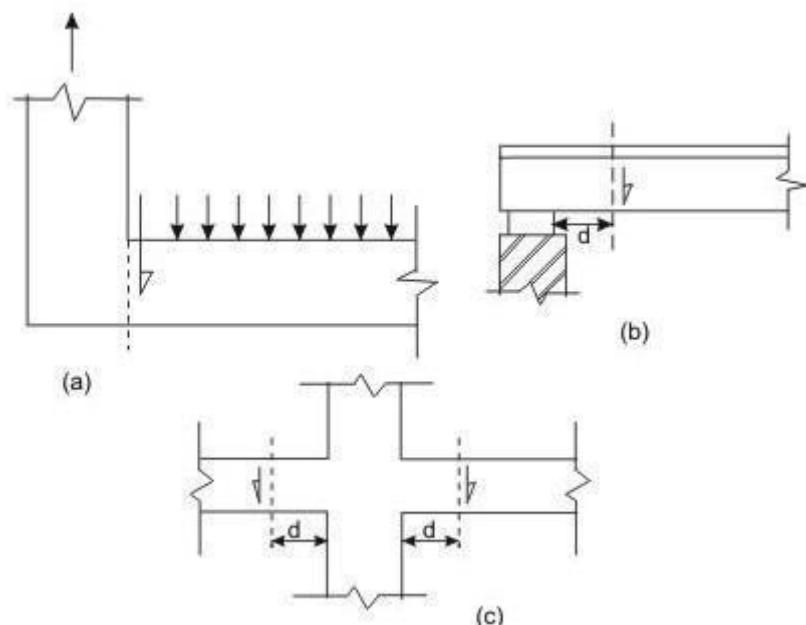

Clauses 22.6.2 and 22.6.2.1 stipulate the critical section for shear and are as follows:

For beams generally subjected to uniformly distributed loads or where the principal load is located further than  $2d$  from the face of the support, where  $d$  is the effective depth of the beam, the critical sections depend on the conditions of supports as shown in Figs. a, b and c and are mentioned below.

- (a) When the reaction in the direction of the applied shear introduces tension (Fig.a) into the end region of the member, the shear force is to be computed at the face of the support of the member at that section.
- (b) When the reaction in the direction of the applied shear introduces compression into the end region of the member (Figs. b and c), the shear force computed at a distance  $d$  from the face of the support is to be used for the design of sections located at a distance less than  $d$  from the face of the support. The enhanced shear strength of sections close to supports, however, may be considered as discussed in the following section

#### **Minimum Shear Reinforcement (cls. 40.3, 26.5.1.5 and 26.5.1.6 of IS 456)**

Minimum shear reinforcement has to be provided even when  $\tau_v$  is less than  $\tau_c$  given in Table 19 as recommended in cl. 40.3 of IS 456. The amount of minimum shear reinforcement, as given in cl. 26.5.1.6, is given below.

The minimum shear reinforcement in the form of stirrups shall be provided such that

$$\frac{A_{sv}}{bs_v} \geq \frac{0.4}{0.87f_y}$$

Where  $A_{sv}$  = total cross-sectional area of stirrup legs effective in shear

$S_v$  = stirrup spacing along the length of the member

$b$  = breadth of the beam or breadth of the web of the flanged beam

$f_y$  = characteristic strength of the stirrup reinforcement in  $\text{N/mm}^2$  which shall not be greater than  $415\text{N/mm}^2$

Further, cl. 26.5.1.5 of IS 456 stipulates that the maximum spacing of shear reinforcement measured along the axis of the member shall not be more than  $0.75 d$  for vertical stirrups and  $d$  for inclined stirrups at  $45^\circ$ , where  $d$  is the effective depth of the section. However, the spacing shall not exceed 300 mm in any case.

#### **Design of Shear Reinforcement (cl. 40.4 of IS 456)**

When  $\tau_v$  is more than  $\tau_c$  given in Table 19 of IS 456:2000, shear reinforcement shall be provided in any of the three following forms:

- (a) Vertical stirrup
- (b) Inclined stirrup
- (c) Bent up bars alongwith stirrups

In the case of bent-up bars, it is to be seen that the contribution towards shear resistance of bent-up bars should not be more than fifty per cent of that of the total shear reinforcement.

The amount of shear reinforcement to be provided is determined to carry a shear force  $V_{us}$  equal to  $V_u - \tau_c bd$

Where  $b$  is the breadth of rectangular beams or  $b_w$  in the case of flanged beams

The strengths of shear reinforcement  $V_{us}$  for the three types of shear reinforcement are as follows:

(a) **Vertical stirrups** ,  $V_{us} = 0.87f_y A_{sv} d \times (1/s_{sv})$

(b) **Inclined stirrup** ,  $V_{us} = \frac{0.87f_y A_{sv} d (\sin\alpha + \cos\alpha)}{s_v}$

(c) **Bent up bars**,  $V_{us} = 0.87f_y A_{sv} \sin\alpha$

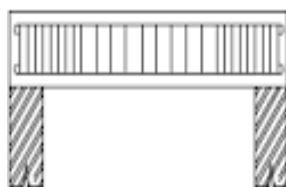


Figure 1 - Vertical Stirrups

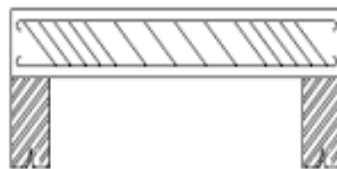


Figure 2 - Inclined Stirrups

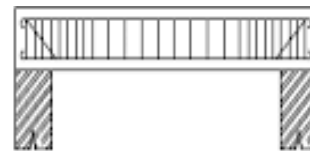


Figure 3 - Bent-up bars with Vertical Stirrups

### Question 1:

A tee beam section having 230 mm width of rib and 460 mm effective depth is reinforced with 5 nos. of 16 mm dia. Bars as tension reinforcement. The section is subjected to a factored shear of 52.5 kN. Check the shear stress and design the shear reinforcement. The materials are M20 grade concrete and Fe415 grade steel. For stirrups mild steel bars may be used.

### Solution:

$$V_u = 52.5 \text{ kN}$$

$$A_{st} = 1005.31 \text{ mm}^2$$

$$\text{Nominal shear stress, } \tau_v = \frac{V_u}{bd} = \frac{52.5 \times 10^3}{230 \times 460} = 0.496 \text{ N/mm}^2$$

$$P_t = \frac{100A_{st}}{bd} = \frac{100 \times 1005.31}{230 \times 460} = 0.95$$

From table 19 of IS 456,  $\tau_c = 0.608 \text{ N/mm}^2$

Here  $\tau_v < \tau_c$ , therefore only nominal shear reinforcement is required.

Select 6 mm dia M.S bars for stirrups

$$A_{sv} = \frac{2 \times \pi \times 6^2}{4} = 56 \text{ mm}^2 \text{ for two legged stirrups}$$

$$\text{For minimum shear reinforcement} = \frac{A_{sv}}{bs_v} \geq \frac{0.4}{0.87f_y}$$

$$\frac{56}{230 \times s_v} \geq \frac{0.4}{0.87 \times 415}$$

$$S_v \leq 132.4 \text{ mm}$$

The spacing shall not exceed

$$(a) 0.75d = 0.75 \times 460 = 345 \text{ mm}$$

$$(b) 300 \text{ mm}$$

Provide 6 mm dia two legged stirrup @ 130 mm c/c

### Question 2:

A tee beam section having 230 mm width of rib and 460 mm effective depth is reinforced with 5 nos. of 16 mm dia. Bars as tension reinforcement. The section is subjected to a factored shear of 90 kN. Check the shear stress and design the shear reinforcement. The materials are M20 grade concrete and Fe415 grade steel. For stirrup mild steel bars may be used.

### Solution:

$$V_u = 90 \text{ kN}$$

$$A_{st} = 1005.31 \text{ mm}^2$$

$$\text{Nominal shear stress, } \tau_v = \frac{V_u}{bd} = \frac{90 \times 10^3}{230 \times 460} = 0.85 \text{ N/mm}^2$$

$$P_t = \frac{100A_{st}}{bd} = \frac{100 \times 1005.31}{230 \times 460} = 0.95$$

$$\text{From table 19 of IS 456, } \tau_c = 0.608 \text{ N/mm}^2$$

Here  $\tau_v > \tau_c$ , therefore shear reinforcement shall be designed.

$$\text{Shear resistance of concrete} = V_{uc} = \tau_c bd = 0.608 \times 230 \times 460 \times 10^{-3} = 64.33 \text{ kN}$$

$$V_{us} = V_u - \tau_c bd = 90 - 64.33 = 25.67 \text{ kN}$$

Using 6 mm dia two legged M.S bars for stirrups

$$A_{sv} = \frac{2 \times \pi \times 6^2}{4} = 56 \text{ mm}^2$$

$$S_v = \frac{0.87f_y A_{sv} d}{V_{us}} = \frac{0.87 \times 250 \times 56.55 \times 460}{25.67 \times 10^3}$$

$$S_v = 220 \text{ mm}$$

The spacing shall not exceed

(a)  $0.75d = 0.75 \times 460 = 345 \text{ mm}$

(b) 300 mm

Provide 6 mm dia two legged stirrup @ 130 mm c/c

**Question 3:**

A tee beam section having 230 mm width of rib and 460 mm effective depth is reinforced with 5 nos. of 16 mm dia. bars as tension reinforcement and out of which 02 nos. bar are bent up at  $45^\circ$ . The section is subjected to a factored shear of 120 KN. Check the shear stress and design the shear reinforcement. The materials are M20 grade concrete and Fe415 grade steel. For stirrups mild steel bars may be used.

**Solution:**

$$V_u = 120 \text{ KN}$$

$$\text{Nominal shear stress, } \tau_v = \frac{V_u}{bd} = \frac{120 \times 10^3}{230 \times 460} = 1.13 \text{ N/mm}^2$$

2 bars are bent up

$$A_{st} = \frac{2\pi 16^2}{4} = 402 \text{ mm}^2$$

$$V_{us} = 0.87 f_y A_{sv} \sin \alpha = 0.87 \times 415 \times 402 \times \sin 45^\circ \\ = 102.63 \text{ KN}$$

For the remaining 3 bars

$$\frac{100 A_s}{bd} = \frac{100 \times 3 \times \frac{\pi}{4} \times 16^2}{230 \times 460} = 0.57$$

$$\tau_c = 0.50 \text{ N/mm}^2$$

$$V_{uc} = \tau_c bd = 0.50 \times 230 \times 460 \times 10^{-3} = 52.90 \text{ KN}$$

$$V_{us} = V_u - \tau_c bd = 120 - 52.90 = 67.10 \text{ KN}$$

$$\text{Shear resistance provided by bent up bars} = 67.10/2 = 33.55 \text{ KN}$$

$$\text{Shear resistance taken up by stirrups} = 67.10 - 33.55 = 33.55 \text{ KN}$$

Use 6 mm dia two legged stirrups to resist 33.55 KN

$$A_{sv} = \frac{2 \times \pi \times 6^2}{4} = 56 \text{ mm}^2$$

$$S_v = \frac{0.87 f_y A_{sv} d}{V_{us}} = \frac{0.87 \times 250 \times 56.55 \times 460}{33.55 \times 10^3} = 168.64 \text{ mm}$$

The spacing shall not exceed

(a)  $0.75d = 0.75 \times 460 = 345 \text{ mm}$

(b) 300 mm

Provide 6 mm dia two legged stirrup@130 mm c/c


## **DEVELOPMENT LENGTH**

### **Introduction:**

- i) One of the most important assumption in the behavior of reinforced concrete structure is that there is proper bond between concrete and reinforcing bar.
- ii) When a RCC element is loaded, the load is first borne by concrete and is then transferred to steel reinforcement.
- iii) This transfer from concrete to steel can be effected only when there is no relative movement or slip or sliding between them when any one these two is strained. The force which prevent the slippage between the two constituent material is known as bond.
- iv) When steel bar are embedded in concrete, the concrete after setting adheres to the surface of the bar and thus resists any force that tends to pull or push this rod. The intensity of this adhesive force is called bond stress.
- v) The bond stresses are the longitudinal shearing stresses acting on the surface between steel and concrete along its length.
- vi) Bond stress is also known as the interfacial shear. Hence bond stress is the shear stress acting parallel to the reinforcing bar on the interface between the bar and the concrete.

### Types of bond:

1. Flexural bond or local bond
2. Anchorage bond or development bond

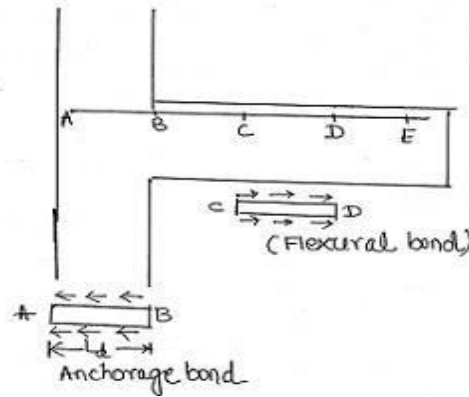

### Flexural bond:

- (i) Flexural bond is one which arises from change in tensile force carried by the bar, along its length, due to change in bending moment along the length of the member. Flexural bond will be more critical at points where shear force is significant.
- (ii) Anchorage bond is that which arises over the length of anchorage provided for a bar. It also arises near the end or cutoff point of a reinforcing bar. The anchorage bond resists the pulling out of the bar if it is in tension or pushing in of the bar if it is in compression.

### Anchorage bond stress:

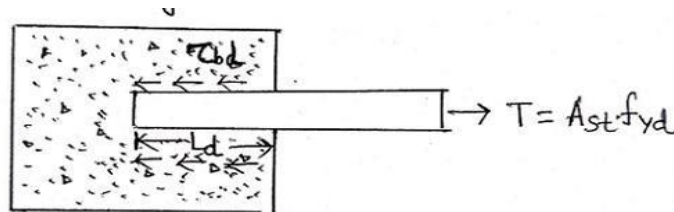


Figure shows a steel bar embedded in concrete and is subjected to a tensile force  $T$ . Due to this force there will be a tendency of the bar to slip out and this tendency is resisted by the bond stress developed over the perimeter of the bar along the length.

The required length necessary to develop full resisting force is called anchorage length in case of axial tension or compression and development length in case of flexural tension and is designated as  $L_d$ .

Hence if  $\phi$  is the nominal diameter of the bar we have

$$(\pi/4)\phi^2 f_y = \tau_{bd} \pi \phi L_d$$

$$L_d = \phi f_y / 4 \tau_{bd}$$

Where  $f_y$  is the design stress in steel  $= 0.87f_y$

$$L_d = 0.87f_y \phi / 4\tau_{bd}$$

So this indicates that a bar must extend a length  $L_d$  beyond any section at which it is required to develop its full strength so that sufficient bond resistance can be developed.

### Design bond stress :


- (i) The design bond stress in limit state method for plain bars in tension shall be as given in clause no.26.2.1.1 of IS: 456

Grade of concrete	M20	M25	M30	M35	M40 and above
Design bond stress $\tau_{bd}$ in $N/mm^2$					


- (ii) Design bond stress for deformed bars in tension –  
For deformed bars these values shall be increased by 60%
- (iii) Design bond stress for bars in compression –  
For bars in compression, the values of bond stress for bars in tension shall be increased by 25%.

### Standard hooks and bends for end anchorage : Anchorage length:

- (i) The development length required at the end of a bar is known as anchorage length.
- (ii) Space available at the end of the beam is limited to accommodate the full development length ( $L_d$ ). In that case hooks or bends are provided. The anchorage value ( $L_e$ ) of hooks or bend is accounted as contribution to the development length ( $L_d$ ).
- (iii) The minimum radius specified for a hook is  $2\phi$  for mild steel bar and  $4\phi$  for high yield bar.
- (iv) In the case of deformed bars the value of bond stress for various grades of concrete is greater by 60% than the plain bars. Hence the deformed bars may be used without hooks provided anchorage requirements are satisfied.
- (v) The length of straight bars beyond the end of the curve should be atleast 4 times the diameter of the bars.



(a) Standard hook



Minimum k for (i) mild steel = 2, and  
(ii) cold worked steel = 4

(b) Standard 90° bend

### Code requirement for anchoring reinforcing bars:

(i) **Anchoring bars in tension :**

Deformed bars may be used without end anchorages provided development length requirement is satisfied. Hooks should normally be provided for plain bars in tension. The anchorage value of bend shall be taken as 4 times the diameter of bar for each 45 bend subjected to a maximum of 16 times the diameter of the bar. The anchorage value of standard U- type hook shall be equal to 16 times the diameter of the bar.


(ii) **Anchoring bars in compression :**

The anchorage length of straight bar in compression shall be equal to the development length of bars in compression.


(iii) **Anchoring shear reinforcement :**

Inclined bars – The development length shall be as for bars in tension : this length shall be measured as under :

- (i) In tension zone from the end of the sloping or inclined portion of the bar.
- (ii) In compression zone from mid depth of the beam

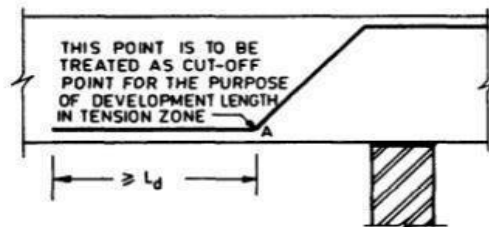


4.2A IN TENSION ZONE

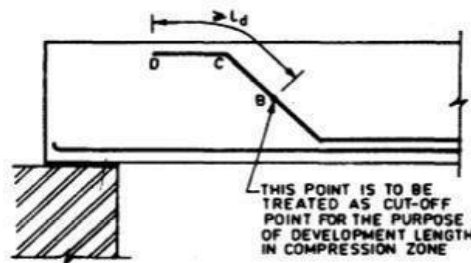

4.2B IN COMPRESSION ZONE

Stirrups –

When the bar is bent through an angle of at least 90° round a bar of at least it will continued beyond the end of the curve for a length of atleast eight diameter or when the bar is bent through an angle of 135 and is continued beyond the end of the curve for a length of at least six bar diameter or when the bar is bent through an angle of 180 and is continued beyond the end of the curve for a length atleast four bar diameter.

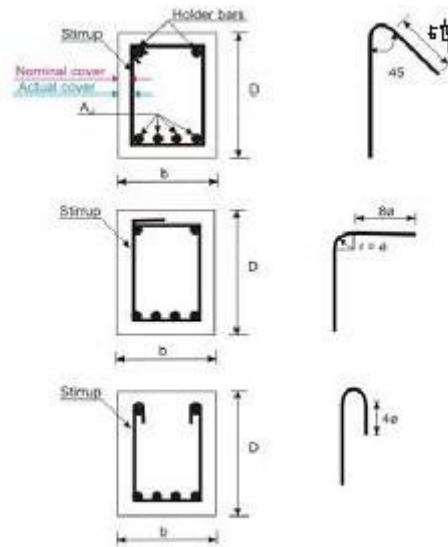

### Checking development length of tension bars:

The stress in a reinforcing bar, at every section must be developed on both side of the section. This is done by providing development length  $L_d$  to both the sides of the section. Such a development length is usually available at mid span location where positive (or sagging) B.M is maximum for simply supported beams. Similarly such a development length is usually available at the intermediate support of a continuous beam where negative ( or hogging) B.M is maximum. Hence no special checking is necessary for such locations. But special checking for development length is essential at following locations;

- i) At simple supports.
- ii) At Cantilever supports.
- iii) At point of contraflexure.
- iv) At point of bar cut off.

### Requirement of development length:

The code stipulates that at the simple support the positive moment tension reinforcement shall be limited to a diameter such that

$$L_d \leq (M_1/V) + L_0$$

Where  $L_d$  = development length

$M_1$  = M.R of the section assuming all reinforcement at the section to be stressed to  $f_{yd}$

$V$  = shear force at the section due to design loads

$L_0$  = sum of anchorage beyond the centre of support and the value of  $L_0$  is limited to  $d$  or  $12\phi$

whichever is greater

The code further recommends that the value of  $M_1/V$  may be increased to 30% when the ends of the reinforcement are confined by a compressive reaction. Such situation arises when a beam is simply supported over a wall.

Thus at simple supports where the compressive reaction confines the ends of reinforcing bar, we have

$$L_d \leq 1.3(M_1/V) + L_0$$

### Question 1:

Calculate the anchorage length in tension and compression for

- (a) Single mild steel bar of dia  $\phi$  in concrete of grade M20
- (b) An HYSD bar of grade Fe415 of dia  $\phi$  in concrete of grade M20

### Solution :

- (a) M.S bar

#### In tension:

Design stress for M.S bar  $= \sigma_s = 0.87f_y = 0.87 \times 250 = 217.5 \text{ N/mm}^2$

$$\tau_{bd} = 1.2 \text{ N/mm}^2$$

anchorage length = development length#

$$= 0.87f_y\phi/4\tau_{bd}$$

$$= 217.5\phi/4 \times 1.2$$

$$= 45.3\phi \text{ or } 46\phi$$

#### Compression:

$$\sigma_s = 0.87f_y = 0.87 \times 250 = 217.5 \text{ N/mm}^2$$

$$\tau_{bd} = 1.2 \times 1.25 \text{ (for compression)} = 1.5 \text{ N/mm}^2$$

$$L_d = 0.87f_y\phi/4\tau_{bd} = 217.5\phi/4 \times 1.5$$

$$= 36.3\phi = 37\phi$$

- (b) HYSD bar

#### Tension :

$$\sigma_s = 0.87f_y = 0.87 \times 415 = 361 \text{ N/mm}^2$$

$$\tau_{bd} = 1.2 \times 1.6 \text{ (HYSD bar)} = 1.92 \text{ N/mm}^2$$

$$L_d = 361\# / 4\tau_{bd} = 217.5\phi / 4 \times 1.92 = 47\#$$

**Compression :**

$$\sigma_s = 0.87f_y = 0.87 \times 415 = 361 \text{ N/mm}^2$$

$$\tau_{bd} = 1.2 \times 1.6 \text{ (HYSD bar)} \times 1.25 \text{ (comp)} = 2.4 \text{ N/mm}^2$$

$$L_d = 361\# / 4\tau_{bd} = 217.5\phi / 4 \times 2.4 = 37.6\# = 38\#$$

**Question 2:**

A simply supported beam is 25 cm by 50 cm and has 2-20 mm HYSD bars going into the support. If the shear force at the centre of support is 110 kN at working loads, determine the anchorage length. Assume M20 mix and Fe415 grade steel.

**Solution:**

$$\text{Factored S.F} = 1.5 \times 110 = 165 \text{ kN}$$

$$A_{st} = 2 \times (\pi/4) d^2 = 628 \text{ mm}^2$$

Assuming 25 mm clear cover to the longitudinal bar

$$\text{Effective depth} = 500 - 25 - (20/2) = 465 \text{ mm}$$

$$F_y = 415 \text{ N/mm}^2$$

$$M_1 = 0.87f_y A_{st} (d - 0.42x_u)$$

$$X_u = \frac{0.87 f_y A_{st}}{0.36 f_{ck} b}$$

$$= \frac{0.87 \times 415 \times 628}{0.36 \times 20 \times 250} = 125.97 = 126 \text{ mm}$$

$$X_{u_{\max}} = 0.48d = 0.48 \times 465 = 223.2 \text{ mm}$$

$$X_u < X_{u_{\max}}$$

$$M_1 = 0.87 \times 415 \times 628 (465 - 0.42 \times 126)$$

$$= 93.43 \times 10^6 \text{ Kmm}$$

$$\tau_{bd} = 1.2 \times 1.6 = 1.92$$

$$L_d = 0.87 \times 415 \phi / 4 \times 1.92$$

$$= 47\phi$$

If the bar is given 90° bend at the centre of the support its anchorage value  $L_0 = 8\phi = 8 \times 20 = 160 \text{ mm}$

$$L_d \leq 1.3(M_1/V) + L_0$$

$$47\phi \leq \frac{1.3 \times 93.45 \times 10^6}{165 \times 10^3} + 160$$

$$\Phi \leq 19 \text{ mm}$$

since actual bar diameter of 20 mm is greater than 19 mm there is a need to increase the anchorage

length  $L_0$  to  $12\phi$  i.e 240 mm

$$L_d \leq 1.3(M_1/V) + L_0$$

$$47\phi \leq \frac{1.3 \times 93.45 \times 10^6}{165 \times 10^3} + 240$$

$$\Phi \leq 20.8 \text{ mm}$$

## **DESIGN OF BEAMS**

### **Design procedure:**

The procedure for design of a beam may be summarized as follows:

- (i) Estimation of load:
  - The correct estimation of loads, a beam has to bear, leads to an economical and safe design of the beams.
  - A designer should not forget to account for any possible load acting on the structure as it leads to an under design of the member and subsequent failure of the beam.
  - The dead load on the beam may be self weight of the beam, floor finish, partitions and some special fixed load if specified.
  - The live loads shall be different for different structure depending on the functional use of the structure.
- (ii) Analysis:
  - Using the above determined loads, the shear force and bending moment are found out and diagrams drawn.
- (iii) Design :

After analysis design the beam as follows:

  - Using the maximum moment, calculate the depth of beam required for balanced section.
  - Find out the steel area required for design moment.
  - Check the shear stress and development length of bars.
  - If some bars are curtailed, check for curtailment using curtailment rules.
  - Check the deflection and cracking using rules for control of deflection and cracking.
  - Draw complete sketches of designed beam with elevation and section.

### Basic rules for design:

(i) Effective span :

Simply supported beam or slab: The effective span of a member that is not built integrally with its support shall be taken as clear span plus the effective depth of slab or beam or centre to centre of support whichever is less. (IS:456 clause no. 22.2 (a))

(ii) Control of deflection:

The deflection of a structure or part there of shall not adversely affect the appearance or efficiency of the structure or finishes or partitions. For beams and slabs the vertical deflection limit may generally be assumed to be satisfied provided that the span to depth ratios are not greater than the values obtained as below: (IS:456 clause No. 23.2.1(a))

(a) Basic values of span to effective depth ratios for span upto 10 m:

Cantilever----- 7  
Simply supported-----20  
Continuous ----- 26

(b) For span above 10 m the value in (a) may be multiplied by a factor  $10/\text{span}$  in meter except in case of cantilever.

(c) Depending on the area and the type of steel for tension reinforcement the vales in (a) & (b) shall be multiplied by modification factor as per graph on pg no.38 of IS: 456

$$F_s = \text{the steel stress of service loads} \\ = 0.58f_y \text{ (area of cross section of steel required/area of cross section of steel provided)}$$

(iii) Reinforcement in beams:

(a) Tension reinforcement :

Minimum reinforcement – the minimum area of the tension reinforcement shall not be less than that given by the following: (IS:456 clause No. 26.5.1.1 (a))

$$\frac{A_{st}}{bd} = \frac{0.85}{f_y}$$

Maximum reinforcement – the maximum area of tension reinforcement shall not exceed  $0.04bD$  (IS:456 clause No. 26.5.1.1 (b))

(b) Compression reinforcement:

Maximum reinforcement – the maximum area of compression reinforcement shall not exceed  $0.04bD$  (IS:456 clause No. 26.5.1.2)

(iv) Criteria for development length:

- According to clause 26.2 of IS:456, the calculated tension or compression in any bar at any section shall be developed on each side of the section by an appropriate development length.
- No bar can be bent up or curtailed upto a distance of development length from the point of maximum moment.

- For example for Fe415 grade reinforcement, the development length in concrete of grade M20 in tension is  $47\phi$ . If 20 mm diameter bar is used, the bars cannot be bent or curtailed upto a distance of  $47 \times 20 = 940$  mm from the point of maximum bending moment.
- The code stipulates that at the simple support the positive moment tension reinforcement shall be limited to a diameter such that

$$L_d \leq (M_1/V) + L_0$$

Where  $L_d$  = development length

$M_1$  = M.R of the section assuming all reinforcement at the section to be stressed to  $f_{yd}$

$V$  = shear force at the section due to design loads

$L_0$  = sum of anchorage beyond the centre of support and the value of  $L_0$  is limited to  $d$  or  $12\phi$  whichever is greater

- The code further recommends that the value of  $M_1/V$  may be increased to 30% when the ends of the reinforcement are confined by a compressive reaction. Such situation arises when a beam is simply supported over a wall. Thus at simple supports where the compressive reaction confines the ends of reinforcing bar, we have

$$L_d \leq 1.3(M_1/V) + L_0$$

(v) Slenderness limit for beams :

To ensure lateral stability of a beam as per clause 23.3 of IS:456

For simply supported and continuous beam

Clear span  $\beta \leq 60b$

$$\beta \leq \frac{250b^2}{d}$$

For cantilever beams

Clear span  $\beta \leq 25b$

$$\beta \leq \frac{100b^2}{d}$$

### Question 1:

A simply supported rectangular beam of 6m span carries a uniformly distributed characteristic load of 24 KN/m inclusive of self weight. Design the beam. The materials are grade M20 concrete and HYSD reinforcement of grade Fe415. The beam is resting on RCC column.

### Solution:

Factored load =  $1.5 \times 24 = 36$  KN/m

$$M_u = \frac{36 \times 6^2}{8} = 162 \text{ KNm}$$

$$V_u = \frac{36 \times 6}{2} = 108 \text{ KN}$$

(a) Calculation of depth:

Assume width of the section  $b = 300$  mm

$$d_{req} = \sqrt{\frac{M_u}{Q_{lim} \times b}} = \sqrt{\frac{162 \times 10^6}{2.76 \times 300}} = 442.32 \text{ mm}$$

Provide effective depth  $d = 500 \text{ mm}$

Assume clear cover of 30 mm and 20 mm dia Fe415 bar

Overall depth  $= D = 500 + 30 + 10 = 540 \text{ mm}$

(b) Calculation of steel area:

$$A_{st} = \frac{M_u}{0.87 f_y (d - 0.42 x_{u_{max}})} = \frac{162 \times 10^6}{0.87 \times 415 (500 - 0.42 \times 0.48 \times 500)}$$

$$= 1123.97 \text{ mm}^2$$

Provide 4 nos. of 20 mm dia bar giving  $A_{st} = 1256.64 \text{ mm}^2$

Let 2 bars are bent at  $1.25D = 1.25 \times 540 = 675 \text{ mm}$  from the face of the support.

The remaining bars should extend within the support for a distance of  $L_d/3 = \frac{47 \times 20}{3} = 313 \text{ mm}$

(c) Check for development length:

(i) A bar can be bent up at a distance greater than  $L_d = 47\phi$  from the centre of the support i.e  $47 \times 20 = 940 \text{ mm}$

In this case the distance is  $= 3000 - 940 = 2060 \text{ mm}$  (safe)

(ii) For the remaining bars

$$A_{st} = 628 \text{ mm}^2$$

$$M_{ul} = 0.87 f_y A_{st} d \left(1 - \frac{A_{st} f_y}{b d f_{ck}}\right)$$

$$= 0.87 \times 415 \times 628 \times 500 \left(1 - \frac{628 \times 415}{300 \times 500 \times 20}\right)$$

$$= 103.62 \text{ KNm}$$

$$V_u = 108 \text{ KN}$$

$$L_0 = 12\phi \text{ (assumed)}$$

As the reinforcement is confined by compressive reaction

$$L_d \leq 1.3(M_1/V) + L_0$$

$$\frac{\phi \sigma_s}{4 \tau_{bd}} \leq 1.3 \frac{103.62 \times 10^6}{108 \times 10^3} + 12 \times 20$$

$$47\phi \leq 1.3 \frac{103.62 \times 10^6}{108 \times 10^3} + 12 \times 20$$

$$\phi \leq 31.64 \text{ mm}$$

$$\phi \text{ provided} = 20 \text{ mm} \quad (\text{safe})$$

The remaining bars should extend within the support for a distance of  $L_d/3 = \frac{47 \times 20}{3} = 313$  mm. If support Width is 300 mm, the bars extend for  $150 + L_0 = 150 + (12 \times 20) = 390$  mm within the support

(d) Check for shear:

$$V_u = 108 \text{ KN}$$

$$\tau_v = \frac{V_u}{bd} = \frac{108 \times 10^3}{300 \times 500} = 0.72 \text{ N/mm}^2$$

$$100A_s/bd = \frac{100 \times 628}{300 \times 500} = 0.42$$

$$\tau_c = 0.44 \text{ N/mm}^2 < \tau_v$$

hence shear design is necessary.

$$\text{At support, } V_{us} = V_u - V_{uc}$$

$$= (108 \times 10^3) - (0.44 \times 300 \times 500) = 42000 \text{ N}$$

$$= 42 \text{ KN}$$

$$\text{Capacity of bent up bars to resist shear} = 0.87 f_y A_{sv} \sin \alpha$$

$$= 0.87 \times 415 \times 628 \times \sin 45^\circ = 160.33 \text{ KN}$$

$$\text{Bent up bars share } 50\% = 21 \text{ KN}$$

$$\text{Vertical stirrup share } 50\% = 21 \text{ KN}$$

At distance d, where bent up bars are not available

$$V_{us} = 42 \text{ KN}$$

Design stirrup for shear = 42 KN

Using 6mm dia mild steel stirrup

$$A_{sv} = 56 \text{ mm}^2$$

$$V_{us} = \frac{0.87 f_y A_{sv} d}{s_v}$$

$$42 \times 10^3 = \frac{0.87 \times 250 \times 56 \times 500}{s_v}$$

$$s_v = 145 \text{ mm}$$

Spacing should not exceed

$$(i) \quad 0.75d = 0.75 \times 500 = 375 \text{ mm}$$

$$(ii) \quad 300 \text{ mm}$$

$$(iii) \quad 145 \text{ mm}$$

Provide 6mm dia two legged mild steel stirrup @ 140 mm c/c.

(e) Check for deflection:

$$\text{Basic span/d ratio} = 20$$

$$\text{Service stress} = 0.58 f_y \frac{A_{streg}}{A_{stpro}}$$

$$= 0.58 \times 415 \times \frac{1123.97}{1256.64}$$

$$= 215.29 \text{ N/mm}^2$$


$$100 A_s / bd = \frac{100 \times 1256.64}{300 \times 500} = 0.84$$


$$\text{Modification factor} = 1.15$$

$$\text{Span/d permissible} = 20 \times 1.15 = 23$$

$$\text{Actual span/d} = 6000/500 = 12 \quad (\text{safe})$$

**Detailing of beam:**

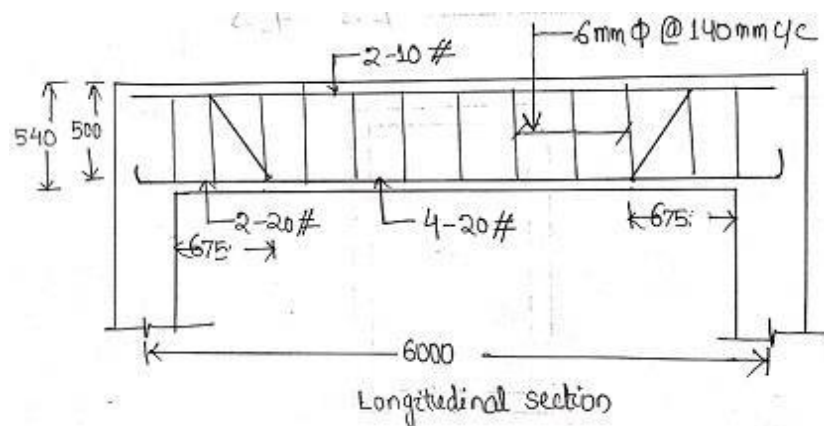

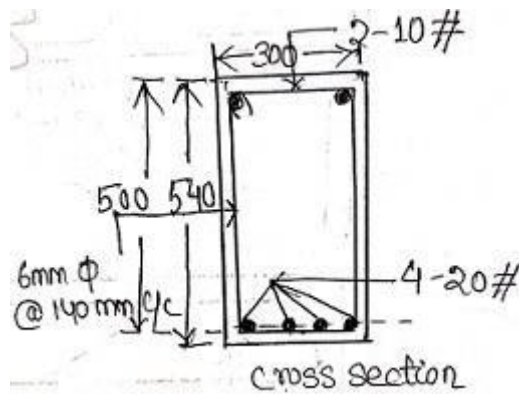

## **ANALYSIS AND DESIGN OF SIMPLY SUPPORTED SLAB**

**Slab** - Slabs are plate elements having the depth  $D$  much smaller than its span and width. They usually carry a uniformly distributed load and form the floor or roof of the building.

They are generally of two types :-

(1) **One way spanning slab-**

- (i) The slab supported on all four edges but  $l_y/l_x > 2$ . Here as  $l_y$  is much more than  $l_x$  then there will be a tendency of the slab to bend in one direction (about  $l_x$ ) only. Hence the slab where  $l_y/l_x > 2$  is called one way slab provided that it is supported on all four edges. (as shown in fig. b)
- (ii) The slab supported on two opposite support is a one way spanning slab. (as shown in fig.a)


(2) **Two way spanning slab-**

If the slab is supported on all four edges and if  $l_y/l_x \leq 2$ , the tendency of the slab is to bend in both direction. Such slabs are called two way spanning slab. (as shown in fig. c)

c)

The following conditions should be satisfied

- (i) The slab shall be supported on all four edges.
- (ii)  $l_y/l_x \leq 2$ .

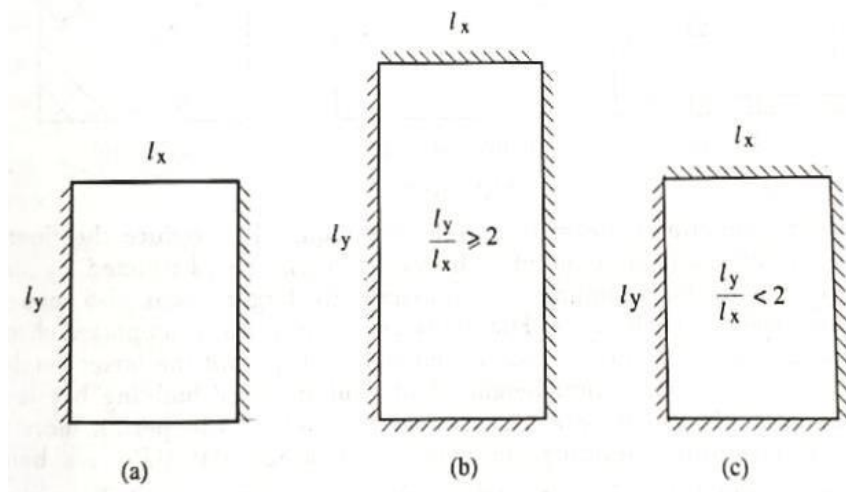

### **Analysis of one way slab :-**

The analysis of the slab spanning in one direction is done by assuming it to be a beam of 1m width.

In addition to the main reinforcement, transverse reinforcement (also called distribution reinforcement) is also provided in a direction at right angles to the main reinforcement. The transverse reinforcement is provided to serve the following purpose-

- (i) It resists the temperature and shrinkage stresses.
- (ii) It keep the main reinforcement in position.
- (iii) It distributes the concentrated and non uniform load throughout the slab more evenly and uniformly.

### **Basic rules for design :-**

- (1) Effective span – Thus in case of freely supported slab the effective span is taken equal to the distance between centre to centre of supports or the clear distance between the supports plus the effective depth of the slab whichever is less.
- (2) ~~Cont of~~ Cantilever -----7

Simply supported ---- 20

Continuous -----26

(3) Reinforcement Requirements:

- (i) Minimum reinforcement- The mild steel reinforcement in either direction in slab shall not be less than 0.15% of the total cross sectional area.  
For HYSD bar this value is 0.12% of the total cross sectional area.
- (ii) Maximum diameter- The diameter of the bar shall not exceed one eighth of the total thickness of the slab.
- (iii) Minimum diameter- SP:34 gives the guideline for minimum diameter of bars in slabs.  
Accordingly, for main bars the minimum diameter shall be 10 mm for plain bars and 8 mm for deformed bars. For distribution bars, the minimum diameter shall be 6 mm in any case.

(4) Shear Stress- In normal cases the shear in slabs is not critical. However shear shall be checked in accordance with the code requirements of clause 40.2. For solid slab the design shear strength in concrete shall be  $\tau_{\text{c}}$ .

(5) Deflection- This shall be checked in the same manner as the beams. The slabs are thin elements and deflection may govern the thickness of the slab.

(6) Cracking- To ensure that the cracking of the slabs is not excessive, spacing of the reinforcement shall be limited to the followings:

For main bars, spacing  $\beta 3d$

$\beta 300 \text{ mm}$

For secondary bars, spacing  $\beta 5d$

$\beta 450 \text{ mm}$

Where  $d$  = Effective depth of slab .

(7) Cover: For mild exposure, specified clear cover is 20 mm. This can be reduced by 5 mm when the reinforcement of 12 mm diameter or less is used.

(8) Development Length : The development length in the slab shall be checked in the same manner as for beams.

For checking development length,  $L_0$  may be assumed as  $8\phi$  for HYSD bars (usually end anchorage is not provided) and  $12\phi$  for mild steel.

**Question 1:**

A simply supported one way slab of clear span 3.0 m is supported on masonry walls of thickness 350 mm. slab is used for residential loads. Design the slab. The materials are grade M20 concrete and HYSD reinforcement of grade Fe415. Live load shall be  $2 \text{ KN/m}^2$ .

**Solution:**

Assume overall depth of slab  $D = 130 \text{ mm}$

(a) Load calculation:

Dead load	$= 0.13 \times 25 = 3.25 \text{ KN/m}^2$
Floor finish	$= 1.00 \text{ kN/m}^2$
Live load	$= 2.00 \text{ KN/m}^2$
Total load	$= 6.25 \text{ KN/m}^2$

$$\text{Factored load} = 1.5 \times 6.25 = 9.4 \text{ kN/m}^2$$

$$\text{Effective span (1)} = 3000 + 350 = 3350 \text{ mm c/c support}$$

$$3000 + 110 \text{ (effective depth)} = 3110 \text{ mm}$$

Use 3.11 m effective span.

(b) Calculation of bending moment and shear force:

Consider 1 m length of slab

$$\text{Load} = 9.4 \text{ kN/m}$$

$$\text{Maximum moment} = 9.4 \times 3.11^2 / 8 = 11.36 \text{ kNm.}$$

$$\text{Maximum shear} = 9.4 \times 3/2 = 14.1 \text{ kN (based on clear span)}$$

(c) Calculation of depth:

$$\begin{aligned} d_{\text{req}} &= \sqrt{\frac{M_u}{Q_{\text{lim}} \times b}} \\ &= \sqrt{\frac{11.36 \times 10^6}{2.76 \times 1000}} = 64.15 \text{ mm} \end{aligned}$$

$$\begin{aligned} d_{\text{provided}} &= 130 - 15 \text{ (cover)} - 5 \text{ (assume } 10\phi \text{ bar)} \\ &= 110 \text{ mm} \end{aligned}$$

(d) Calculation of steel area:

$$A_{\text{st}} = \frac{M_u}{0.87 f_y (d - 0.42 x_{\text{u,max}})} = \frac{11.36 \times 10^6}{0.87 \times 415 (110 - 0.42 \times 0.48 \times 110)}$$

$$= 358 \text{ mm}^2$$

$$\text{Spacing} = \frac{\text{area of one bar} \times 1000}{\text{required area in mm}^2 \text{ per metre}}$$

$$= \frac{\frac{\pi \times 8^2}{4} \times 1000}{358} = 140 \text{ mm}$$

$$\text{Provide 8mm dia bar @ 140 mm c/c giving } A_{\text{st}} = \frac{\text{area of one bar} \times 1000}{\text{spacing}} = \frac{\frac{\pi \times 8^2}{4} \times 1000}{140} = 360 \text{ mm}^2$$

$$\text{Half the bars are bent at } 0.1l = 0.1 \times 3100 = 310 \text{ mm}$$

Remaining bars provide 180 mm<sup>2</sup> area.

$$p_t = \frac{100 A_s}{bD} = \frac{100 \times 180}{1000 \times 130} = 0.13 > 0.12$$

i.e remaining bars provide minimum steel. Thus half bars may be bent up.

$$\text{Distribution steel} = \frac{0.15 \times 1000 \times 130}{100} = 195 \text{ mm}^2, \text{ using mild steel}$$

$$\text{Spacing} = \frac{\text{area of one bar} \times 1000}{\text{required area in mm}^2 \text{ per metre}}$$

$$= \frac{\frac{\pi \times 6^2}{4} \times 1000}{195} = 145 \text{ mm}$$

Provide 6mm  $\phi$  @ 140 mm c/c

(e) Check for shear:

For bars at support

$$\begin{aligned} \text{Correct } d &= 130 - 15 - 4 \\ &= 111 \text{ mm} \end{aligned}$$

$$p_t = \frac{100A_s}{bd} = \frac{100 \times 180}{1000 \times 111} = 0.16$$

for slab upto 150 mm thickness,  $k = 1.3$

value of  $\tau_c$  from IS:456 = 0.28 N/mm<sup>2</sup>

design shear strength =  $k\tau_c = 1.3 \times 0.28 = 0.364 \text{ N/mm}^2$

$$\text{actual shear stress} = \tau_v = \frac{14.1 \times 10^3}{1000 \times 111} = 0.13 \text{ N/mm}^2 < 0.364 \text{ N/mm}^2 \quad (\text{safe})$$

(f) Check for development length:

For continuing bars,  $A_{st} = 180 \text{ mm}^2$ . Also, the ends of the reinforcement are confined by compressive reaction.

$$\begin{aligned} M_{ul} &= 0.87 f_{yk} A_{st} d \left( 1 - \frac{A_{st} f_{yk}}{b d f_{ck}} \right) \\ &= 0.87 \times 415 \times 180 \times 111 \left( 1 - \frac{180 \times 415}{1000 \times 111 \times 20} \right) \\ &= 7 \text{ KNm} \end{aligned}$$

$$V_u = 14.1 \text{ KN}$$

$$L_0 = 12 \neq (\text{assumed})$$

$$L_d \leq 1.3(M_1/V) + L_0$$

$$\frac{\phi \sigma_s}{4\tau_{bd}} \leq 1.3 \frac{7 \times 10^6}{14.1 \times 10^3} + 12 \times 8$$

$$47\phi \leq 1.3 \frac{7 \times 10^6}{14.1 \times 10^3} + 96$$

$$\Phi \leq 15.77 \text{ mm}$$

$$\Phi \text{ provided} = 8 \text{ mm} \quad (\text{safe})$$

(g) Check for deflection:

Basic span/d ratio = 20

$$\text{Service stress} = 0.58 f_y \frac{A_{streg}}{A_{stpro}}$$

$$= 0.58 \times 415 \times \frac{358}{360}$$

$$= 240 \text{ N/mm}^2$$


$$100A_s/bd = \frac{100 \times 360}{1000 \times 111} = 0.32$$

Modification factor = 1.5

Span/d permissible =  $20 \times 1.5 = 30$

Actual span/d =  $3100/111 = 28 < 30$  (safe)

**Detailing of slab:**

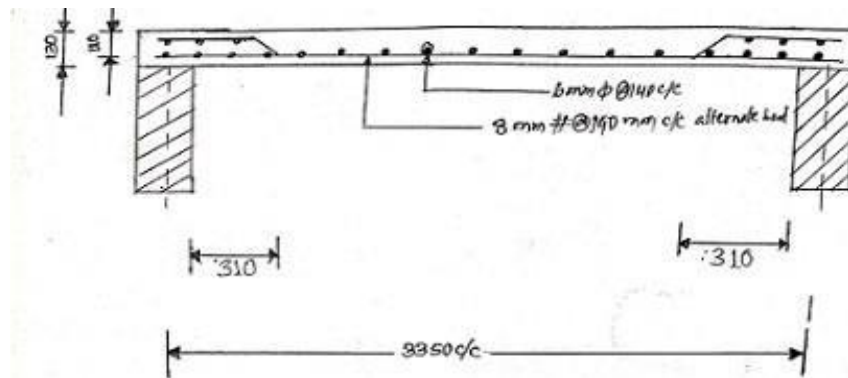

## Two way slab:

- The two way spanning slab occurs when the slab is supported on all four edges and  $l_y/l_x < 2$ .
- Generally when a two – way slab is used, compared to one way slab, the deflection and bending of slab are reduced i.e bending moment is reduced.
- In this type of slab the bending moment is distributed in both the direction. This results in increase in load carrying capacity of the section.
- The two way slab can be simply supported or restrained slab.
- In simply supported slab, the corners can lift away from the support.
- In restrained slab, the corners are held down by edge beams. The corners are held down by means of the stiffness of the beam and therefore at corners torsion is induced.

### Analysis of simply supported two way slab:

#### Computation of bending moment:

- When simply supported slab don't have adequate provision to resist torsion at corner and to prevent the corner from lifting, the maximum moment per unit width are given by the following equation

$$M_x = \alpha_x w l_x^2$$

$$M_y = \alpha_y w l_y^2$$

Where  $M_x$  and  $M_y$  = moments on strips of unit width spanning  $l_x$  and  $l_y$  respectively

$\alpha_x$  and  $\alpha_y$  = coefficient given in table

$l_x$  and  $l_y$  = length of the shorter span and longer span respectively


$w$  = total design load per unit area

Bending moment coefficient for slabs spanning in two direction at right angles, simply supported on four sides

- As per IS : 456 recommendation at least 50% of the tension reinforcement provided at mid span should extend to within  $0.1l_x$  or  $0.1l_y$  of the support.

**Computation of shear force:**

Shear force are computed following the procedure stated below with reference to the figure given below.

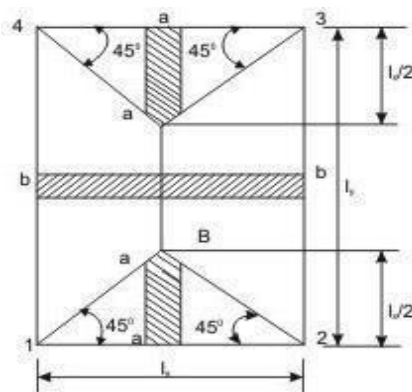

The two – way slab is divided into two triangular and two trapezoidal zones by drawing lines from each corner at an angle of  $45^\circ$ . The loads of triangular segment A will be transferred to beam 1-2 and the loads of trapezoidal segment B will be transferred to beam 2-3. The shear forces per unit width of the strips aa and bb are highest at the ends of strips. Moreover, the length of half the strip bb is equal to the length of the strip aa. Thus, the shear forces in both strips are equal and we can write,

$$V_u = w (l_x/2)$$

$$\tau_v = \frac{V_u}{bd}$$

### Check for deflection:

The deflection of two-way slab shall be checked as per one – way slab. For slab spanning in two directions, the shorter of the two spans should be used for calculating the span to effective depth ratios.

### Question 1:

A drawing room of a residential building measures  $4.3 \text{ m} \times 6.55 \text{ m}$ . It is supported on 350 mm thick walls on all four sides. The slab is simply supported at edges with a provision to resist torsion at corners. Design the slab using M20 concrete and HYSD reinforcement of grade Fe 415.

### Solution:

Consider 1 m wide strip.

Assume 180 mm thick slab with 160 mm effective depth.

$$L_x = 4.3 + 0.16 = 4.46 \text{ say } 4.5 \text{ m}$$

$$L_y = 6.55 + 0.16 = 6.71 \text{ say } 6.75 \text{ m}$$

Load calculation :

$$\text{Dead load} = 0.18 \times 25 = 4.5 \text{ KN/m}^2$$

$$\text{Floor finish} = 1.0 \text{ KN/m}^2$$

$$\text{Live load} = 2.0 \text{ KN/m}^2$$

$$\text{Total} = 7.5 \text{ KN/m}^2$$

For 1 m wide strip

$$P_u = 1.5 \times 7.5 = 11.25 \text{ KN/m}$$

$$l_y/l_x = 6.75/4.5 = 1.5$$

$$M_{ux} = 0.104 \times 11.25 \times 4.5^2 = 23.7 \text{ KNm}$$

$$M_{uy} = 0.046 \times 11.25 \times 4.5^2 = 10.48 \text{ KNm}$$

### Calculation of depth

$$d_{\text{req}} = \sqrt{\frac{23.7 \times 10^6}{1000 \times 2.76}}$$

$$= 92.7 \text{ mm}$$

$$d_{\text{short}} = 180 - 15 (\text{cover}) - 5 (\text{assume } 10\phi \text{ bar})$$

$$= 160 \text{ mm} > 92.7 \text{ mm } d_{\text{long}}$$

$$= 160 - 10 = 150 \text{ mm}$$

### Calculation of steel area

$$\text{Along short span} = \frac{M_u}{bd^2} = \frac{23.7 \times 10^6}{1000 \times 160 \times 160} = 0.926$$

$$p_t = 0.273$$

$$A_{st} = \frac{0.273 \times 1000 \times 160}{100} = 437 \text{ mm}^2$$

$$\text{Along long span} = \frac{M_u}{bd^2} = \frac{10.48 \times 10^6}{1000 \times 150 \times 150} = 0.466$$

$$p_t = 0.129$$

$$A_{st} = \frac{0.129 \times 1000 \times 150}{100} = 194 \text{ mm}^2$$

$$\text{Minimum steel area} = \frac{0.12 \times 1000 \times 180}{100} = 216 \text{ mm}^2$$

Provide 10 mm dia about 180 mm c/c = 436 mm<sup>2</sup> in short span and 8 mm dia about 230 mm c/c = 217 mm<sup>2</sup> in long span.

The bars cannot be bent or curtailed because if 50% of long span bars are curtailed, the remaining bars will be less than minimum.

### Check for development length

$$\text{Long span } V_u = 11.25 \times 2.25 = 25.31 \text{ KN}$$

$$M_{u1} = 0.87 \times 415 \times 217 \times \left(150 - \frac{415 \times 217}{1000 \times 20}\right) \times 10^{-6}$$

$$= 11.40 \text{ KNm}$$

$$\text{Assuming } L_0 = 8\#$$

$$= 1.3 \times \frac{11.40 \times 10^6}{25.31 \times 10^3} + 8\# \geq 47\#$$

$$\# \leq 15.01 \text{ mm}$$

$$\text{Short span } V_u = 11.25 \times 2.25 = 25.31 \text{ KN}$$

$$M_{u1} = 0.87 \times 415 \times 436 \times \left(160 - \frac{415 \times 436}{1000 \times 20}\right) \times 10^{-6}$$

$$= 23.76 \text{ KNm}$$

$$\text{Assuming } L_0 = 8\#$$

$$= 1.3 \times \frac{23.76 \times 10^6}{25.31 \times 10^3} + 8\# \geq 47\#$$

$$\# \leq 31.3 \text{ mm}$$

The bond is usually critical along long direction.

### Check for shear

This is critical along long span

$$\text{Shear stress } \tau_v = \frac{25.31 \times 10^3}{1000 \times 150} = 0.169 \text{ N/mm}^2$$

$$p_t = \frac{100 A_s}{bd} = \frac{100 \times 217}{1000 \times 150} = 0.145$$

$$\tau_c = 0.28 \text{ N/mm}^2$$

$$k\tau_c = 0.28 \times 1.2 = 0.336 \text{ N/mm}^2 \quad (\text{safe})$$

### Check for deflection:

The deflection shall be checked along short span

$$\text{Basic } \frac{\text{span}}{d} \text{ ratio} = 20$$

$$p_t = \frac{100 A_s}{bd} = \frac{100 \times 448}{1000 \times 160} = 0.28$$


$$\text{service stress} = 0.58 \times 415 \times \frac{435}{448} = 234 \text{ N/mm}^2$$


$$\text{modification factor} = 1.5$$

$$\text{permissible } \frac{\text{span}}{d} \text{ ratio} = 20 \times 1.5 = 30$$

$$\text{actual } \frac{\text{span}}{d} \text{ ratio} = \frac{4480}{160} = 28 \quad (\text{safe})$$

### Reinforcement Detailing :

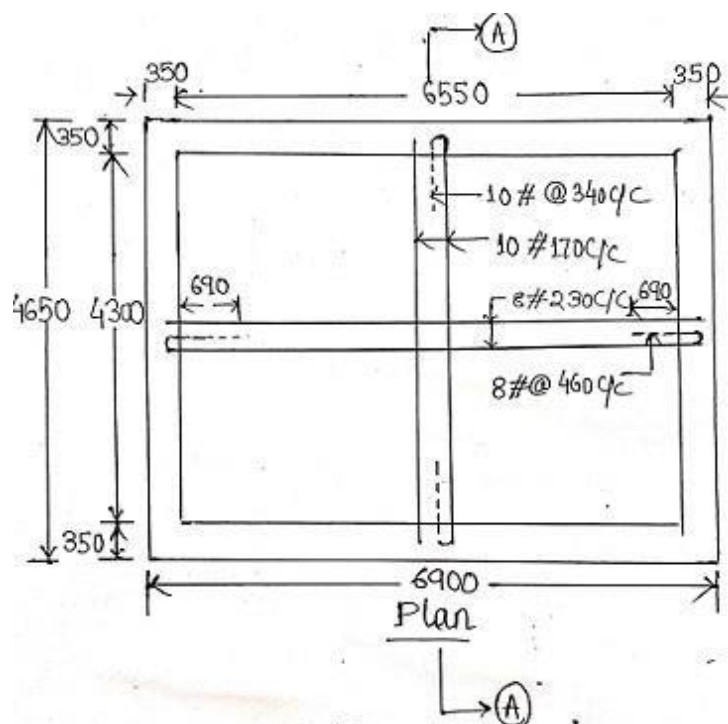

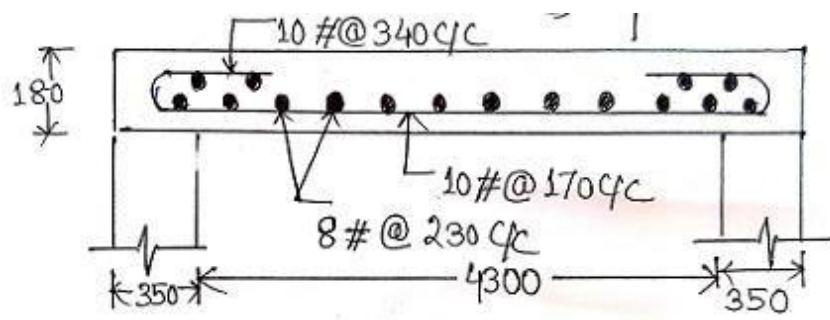

Section A-A

# DESIGN OF COLUMN


## Introduction :

- A compression member whose effective length exceeds three times its least lateral dimension is termed as the column.
- If the effective length is less than three times its lateral dimension s termed as pedestal.
- The column in a building usually carry axial compressive load.
- The shape of a column may be square, rectangular, circular or any other shape depending upon architectural requirement.


## Classification of Columns Based on Types of Reinforcement

Based on the types of reinforcement, the reinforced concrete columns are classified into three groups:


- (i) Tied columns: The main longitudinal reinforcement bars are enclosed within closely spaced lateral ties.
- (ii) Columns with helical reinforcement: The main longitudinal reinforcement bars are enclosed within closely spaced and continuously wound spiral reinforcement. Circular and octagonal columns are mostly of this type.
- (iii) Composite columns: The main longitudinal reinforcement of the composite columns consists of structural steel sections or pipes with or without longitudinal bars.

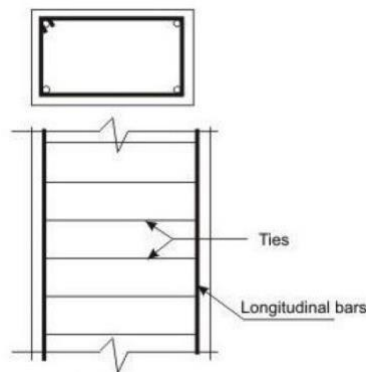


**Tied Column**

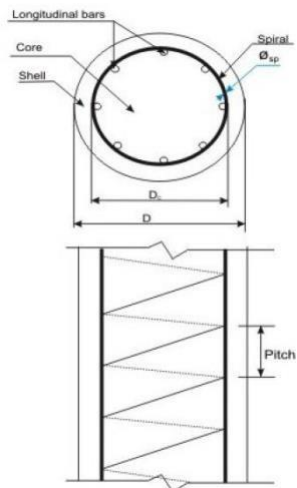

**Column with helical reinforcement**



**Composite column (steel section)**

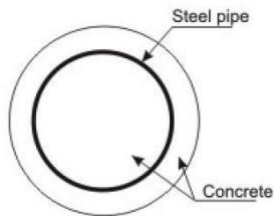

**Composite column (steel pipe)**

Out of the three types of columns, the tied columns are mostly common with different shapes of the cross-sections viz. square, rectangular etc. Helically bound columns are also used for circular or octagonal shapes of cross-sections.

### **Classification of Columns Based on Loadings**

Columns are classified into the three following types based on the loadings:

- (i) Columns subjected to axial loads only (concentric)
- (ii) Columns subjected to combined axial load and uniaxial bending.
- (iii) Column subjected to combined axial load and bi-axial bending

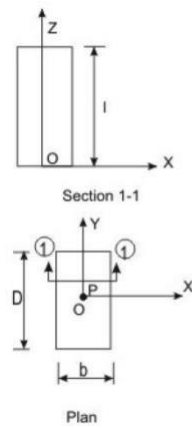


Figure Axial loading (concentric)

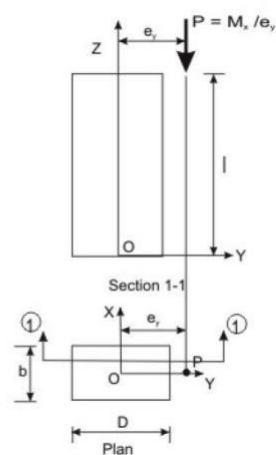


Figure Axial loading with uniaxial bending

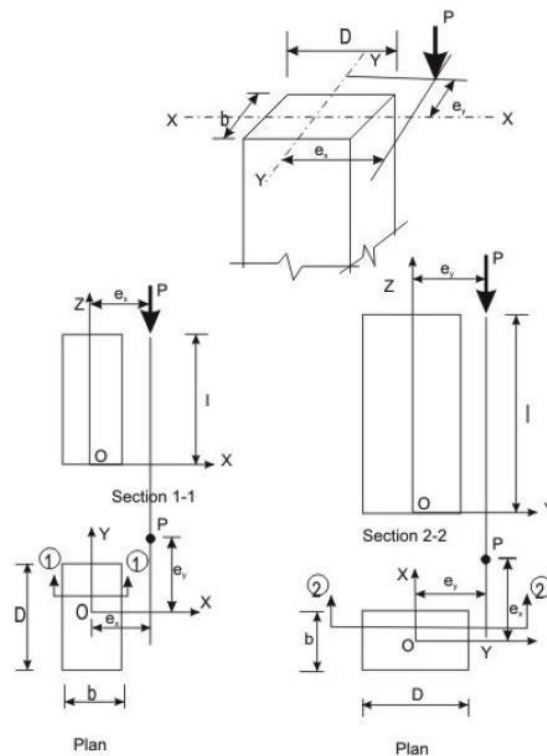


Figure : Axial loading with biaxial bending

### Classification of Columns Based on Slenderness Ratios

Columns are classified into the following two types based on the slenderness ratios:

- (i) Short columns
- (ii) Slender or long columns


## Longitudinal Reinforcement

The longitudinal reinforcing bars carry the compressive loads along with the concrete. Clause 26.5.3.1 stipulates the guidelines regarding the minimum and maximum amount, number of bars, minimum diameter of bars, spacing of bars etc. The following are the salient points:


- (a) The cross sectional area of longitudinal reinforcement shall be not less than 0.8 percent nor more than 6% of the gross sectional area.
- (b) Four and six are the minimum number of longitudinal bars in rectangular and circular columns, respectively.
- (c) The diameter of the longitudinal bars should be at least 12 mm.
- (d) Columns having helical reinforcement shall have at least six longitudinal bars within and in contact with the helical reinforcement. The bars shall be placed equidistant around its inner circumference.
- (e) The bars shall be spaced not exceeding 300 mm along the periphery of the column.
- (f) The amount of reinforcement for pedestal shall be at least 0.15 per cent of the cross- sectional area provided.

## Transverse Reinforcement


Transverse reinforcing bars are provided in forms of circular rings, polygonal links (lateral ties) with internal angles not exceeding 135° or helical reinforcement. The transverse reinforcing bars are provided to ensure that every longitudinal bar nearest to the compression face has effective lateral support against buckling. Clause 26.5.3.2 stipulates the guidelines of the arrangement of transverse reinforcement.

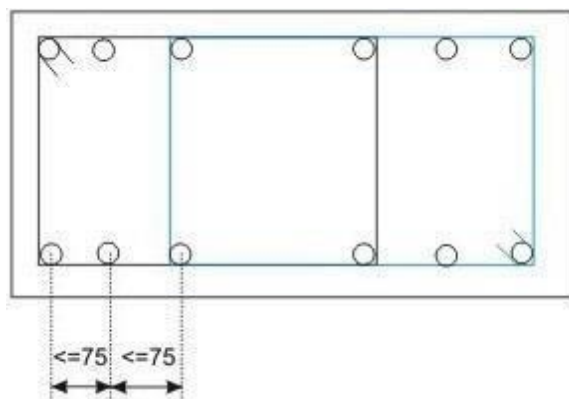

- (a) Transverse reinforcement shall only go round corner and alternate bars if the longitudinal bars are not spaced more than 75 mm on either side as shown in above figure.

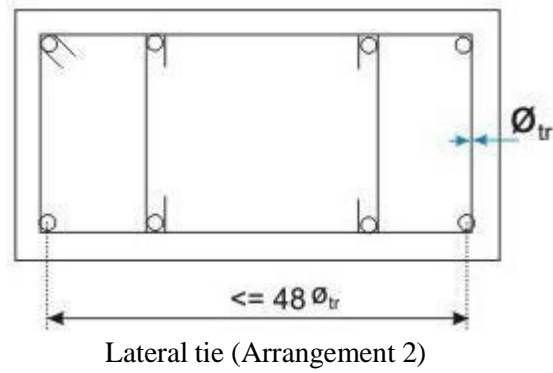


- (b) Longitudinal bars spaced at a maximum distance of 48 times the diameter of the tie shall be tied by single tie and additional open ties for in between longitudinal bars as shown in above figure.

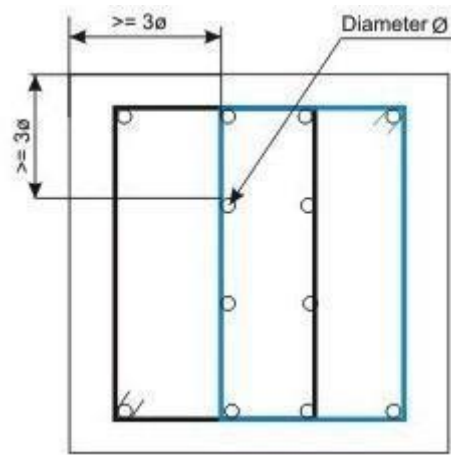

Lateral tie (Arrangement 3)

- (c) For longitudinal bars placed in more than one row : (i) transverse reinforcement is provided for the outer-most row in accordance with (a) above, and (ii) no bar of the inner row is closer to the nearest compression face than three times the diameter of the largest bar in the inner row.

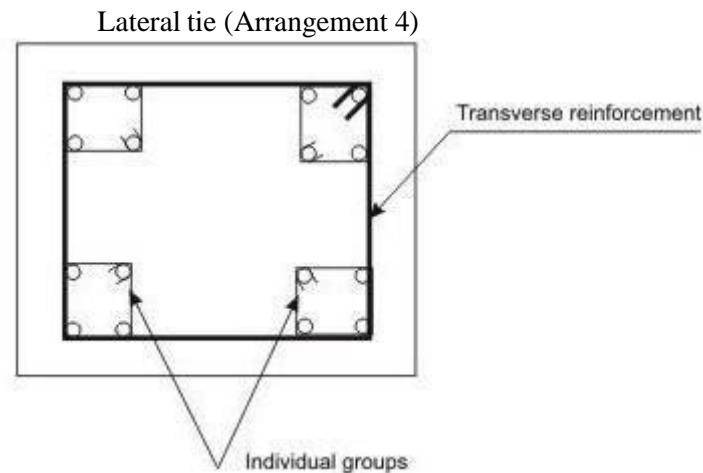

(d) For longitudinal bars arranged in a group such that they are not in contact and each group is adequately tied as per (a), (b) or (c) above, as appropriate, the transverse reinforcement for the compression member as a whole may be provided assuming that each group is a single longitudinal bar for determining the pitch and diameter of the transverse reinforcement. The diameter of such transverse reinforcement should not, however, exceed 20 mm as shown in above figure.

#### **Pitch and Diameter of Lateral Ties**

(a) Pitch: The maximum pitch of transverse reinforcement shall be the least of the following:

- (i) the least lateral dimension of the compression members;
- (ii) sixteen times the smallest diameter of the longitudinal reinforcement bar to be tied; and
- (iii) 300 mm.

(b) Diameter: The diameter of the polygonal links or lateral ties shall be not less than one-fourth of the diameter of the largest longitudinal bar, and in no case less than 6 mm

#### **Cover :**

The longitudinal reinforcing bar in a column shall have concrete cover, not less than 40 mm nor less than the diameter of such bar.

#### **Assumptions in the Design of Compression Members by Limit State of Collapse**

The following are the assumptions in addition to given in 38.1 (a) to (e) for flexure for the design of compression members (cl. 39.1 of IS 456).

- (i) The maximum compressive strain in concrete in axial compression is taken as 0.002.
- (ii) The maximum compressive strain at the highly compressed extreme fibre in concrete subjected to axial compression and bending and when there is no tension on the section shall be 0.0035 minus 0.75 times the strain at the least compressed extreme fibre.

### Minimum Eccentricity

In practical construction, columns are rarely truly concentric. Even a theoretical column loaded axially will have accidental eccentricity due to inaccuracy in construction or variation of materials etc. Accordingly, all axially loaded columns should be designed considering the minimum eccentricity as stipulated in cl. 25.4 of IS 456 and given below (Fig.3.2c)

$$e_{x \min} \geq \text{greater of } (l/500 + D/30) \text{ or } 20 \text{ mm}$$

$$e_{y \min} \geq \text{greater of } (l/500 + b/30) \text{ or } 20 \text{ mm}$$

where  $l$ ,  $D$  and  $b$  are the unsupported length, larger lateral dimension and least lateral dimension, respectively.

### Short axially loaded tied columns:

Factored concentric load applied on short tied columns is resisted by concrete of area  $A_c$  and longitudinal steel of areas  $A_{sc}$  effectively held by lateral ties at intervals. Assuming the design strengths of concrete and steel are  $0.4f_{ck}$  and  $0.67f_y$ , respectively, we can write

$$P_u = 0.4f_{ck}A_c + 0.67f_yA_{sc}$$

Where  $P_u$  = axial load on the member

$f_{ck}$  = characteristic strength of concrete

$A_c$  = area of concrete

$f_y$  = characteristic strength of the compression reinforcement, and

$A_{sc}$  = area of longitudinal reinforcement for columns.

### Problem 1:

A short R.C.C column is to carry a factored load of 1900 kN. If the column is to be a square, design the column. Assume  $e_{\min} < 0.05D$ . the materials are M20 grade concrete and mild steel.

### Solution:

Assume minimum percentage of steel = 0.8 percent of gross sectional area ( $A_g$ )

Area of longitudinal reinforcement =  $A_{sc} = 0.008A_g$

Area of concrete  $A_c = A_g - A_{sc} = 0.992 A_g$

$$P_u = 0.4f_{ck}A_c + 0.67f_yA_{sc}$$

$$1900 \times 10^3 = 0.4 \times 20 \times 0.992 A_g + 0.67 \times 250 \times 0.008A_g$$

$$A_g = 204830 \text{ mm}^2$$

If the column is to be a square, the side of the column = 453 mm

Adopt 450 mm  $\times$  450 mm size column. Then

$$P_u = 0.4f_{ck}A_c + 0.67f_yA_{sc}$$

$$1900 \times 10^3 = 0.4 \times 20 \times (450 \times 450 - A_{sc}) + 0.67 \times 250 \times A_{sc}$$

$$A_{sc} = 1756 \text{ mm}^2$$

Provide 4 no. 20 mm diameter bars plus 4 nos. 16 mm diameter bars giving

$$A_{sc} = 4(314+201) = 2060 \text{ mm}^2$$


**Lateral ties:**

Use 6 mm  $\phi$  lateral ties

Spacing should not exceed

- (i) 450 mm (minimum column dimension)
- (ii)  $16 \phi = 16 \times 16 = 256$  mm
- (iii) 300 mm

Provide 6 mm  $\phi$  lateral ties about 250 mm c/c.

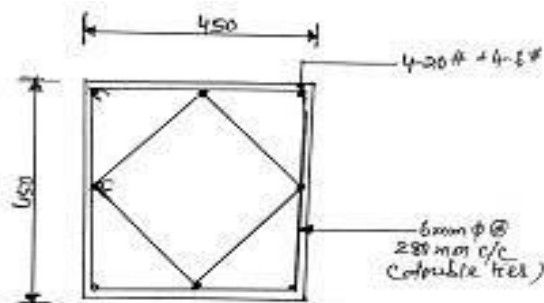

# Design of isolated footing

## Introduction:

Most of the structures built by us are made of reinforced concrete. Here, the part of the structure above ground level is called as the superstructure, where the part of the structure below the ground level is called as the substructure. Footings are located below the ground level and are also referred as foundations. Foundation is that part of the structure which is in direct contact with soil. The R.C. structures consist of various structural components which act together to resist the applied loads and transfer them safely to soil. In general the loads applied on slabs in buildings are transferred to soil through beams, columns and footings. Footings transfer the vertical loads, Horizontal loads, Moments, and other forces to the soil.

The important purpose of foundation is as follows

1. To transfer forces from superstructure to firm soil below.
2. To distribute stresses evenly on foundation soil such that foundation soil neither fails nor experiences excessive settlement.
3. To develop an anchor for stability against overturning.
4. To provide an even surface for smooth construction of superstructure

## Types of foundation:

Based on the position with respect to ground level, Footings are classified into two types;

1. Shallow foundation
2. Deep Foundations

Shallow Foundations are provided when adequate SBC is available at relatively short depth below ground level. Here, the ratio of  $D_f / B < 1$ , where  $D_f$  is the depth of footing and  $B$  is the width of footing

Deep Foundations are provided when adequate SBC is available at large depth below ground level. Here the ratio of  $D_f / B \geq 1$ .

## Types of Shallow foundation :

The different types of shallow foundations are as follows:

- Isolated Footing
- Combined footing
- Strap Footing
- Strip Footing
- Mat/Raft Foundation
- Wall footing

### (a) Isolated column footing:

These are independent footings which are provided for each column. This type of footing is chosen when


- SBC is generally high
- Columns are far apart
- Loads on footings are less

The isolated footings can have different shapes in plan. Generally it depends on the shape of column cross section Some of the popular shapes of footings are;


- Square

- Rectangular
- Circular

The isolated footings essentially consist of bottom slab. These bottom Slabs can be either flat, stepped or sloping in nature. The bottom of the slab is reinforced with steel mesh to resist the two internal forces namely bending moment and shear force.

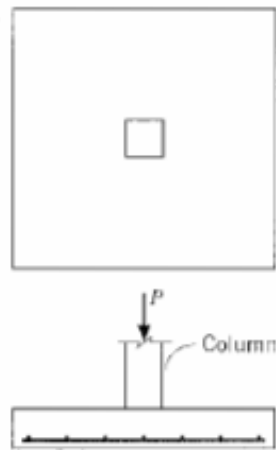

**(b) Combined column footing**

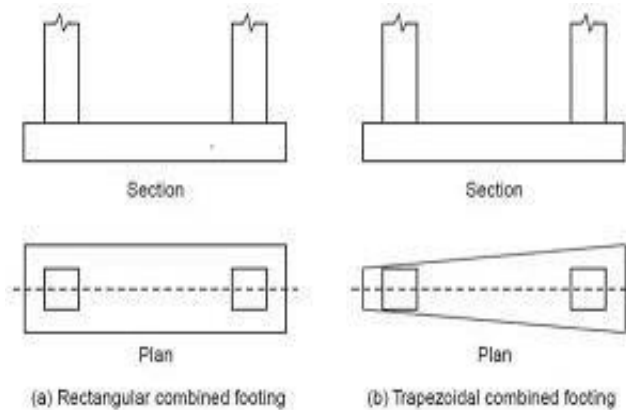


These are common footings which support the loads from 2 or more columns. Combined footings are provided when

- SBC is generally less
- Columns are closely spaced
- Footings are heavily loaded

In the above situations, the area required to provide isolated footings for the columns generally overlap. Hence, it is advantageous to provide single combined footing. In some cases the columns are located on or close to property line. In such cases footings cannot be extended on one side. Here, the footings of exterior and interior columns are connected by the combined footing.


**(c) Strap footing:**

An alternate way of providing combined footing located close to property line is the strap footing. In strap footing, independent slabs below columns are provided which are then connected by a strap beam. The strap beam does not remain in contact with the soil and does not transfer any pressure to the soil. Generally it is used to combine the footing of the outer column to the adjacent one so that the footing does not extend in the adjoining property.

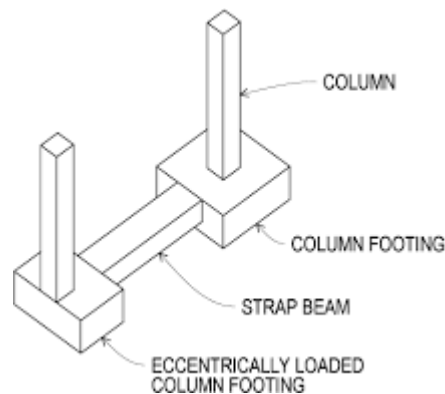

**(d) Strip footing:**


Strip footing is a continuous footing provided under columns or walls. A typical strip footing for columns is shown in Fig

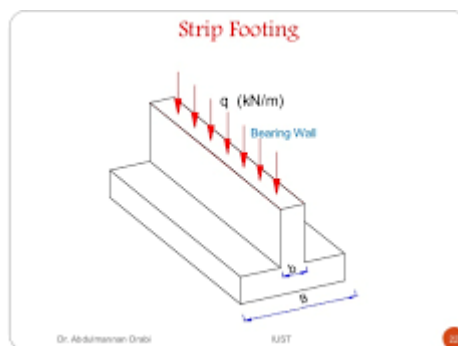

**(e) Mat foundation:**

Mat foundation covers the whole plan area of structure. The detailing is similar to two way reinforced solid floor slabs or flat slabs. It is a combined footing that covers the entire area beneath a structure and supports all the walls and columns. It is normally provided when

- Soil pressure is low
- Loads are very heavy
- Spread footings cover  $> 50\%$  area

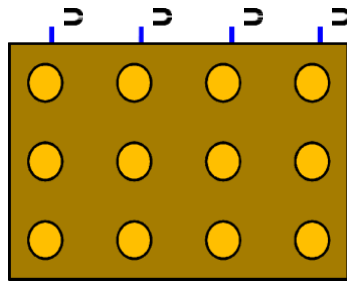

### **Type of deep foundation:**

Deep foundations are provided when adequate SBC is available at large depth below GL. There are different types of deep foundations. Some of the common types of deep foundations are listed below.

- Pile Foundation
- Pier Foundation
- Well Foundation

### **Bearing capacity of soil:**

The safe bearing capacity of soil is the safe extra load soil can withstand without experiencing shear failure. The Safe Bearing Capacity (SBC) is considered unique at a particular site. But it also depends on the following factors:

- Size of footing
- Shape of footing
- Inclination of footing
- Inclination of ground
- Type of load
- Depth of footing etc

Based on ultimate capacity, i.e., shear failure criteria, the SBC is calculated as

$$\text{SBC} = \text{Total load} / \text{Area of footing}$$

Usually the Allowable Bearing Pressure (ABP) varies in the range of 100 KN/m<sup>2</sup> to 400 KN/m<sup>2</sup>. The area of the footing should be so arrived that the pressure distribution below the footing should be less than the allowable bearing pressure of the soil.

### **Design of isolated footing:**

The objective of design is to determine

- Area of footing
- Thickness of footing
- Reinforcement details of footing (satisfying moment and shear considerations)
- Check for bearing stresses and development length

This is carried out considering the loads of footing, SBC of soil, Grade of concrete and Grade of steel. The method of design is similar to the design of beams and slabs. Since footings are buried, deflection control is not important. However, crack widths should be less than 0.3 mm.

**Design steps:**

- Find the area of footing (due to service loads)
- Assume suitable thickness of footing
- Identify critical section for flexure and shear
- Find the bending moment and shear forces at these critical sections (due to factored loads)
- Check the adequacy of the assumed thickness
- Find the reinforcement details
- Check for development length
- Check for bearing stresses

**Cover:**

Clear cover to main reinforcement of the footing bars may be provided as 50 mm for normal soils.

**Size of the footing:**

Assume the weight of the footing as 10% of the axial load on column. If column load is W, the load on soil is 1.1 W.

$$\text{Area of the footing} = \frac{\text{load on soil}}{\text{allowable bearing pressure on soil}}$$


From this area, fix the size of the footing.

**Critical section for bending moment:**

This is determined in accordance with clause 34.2.3 of IS:456 as follows:

The greatest bending moment to be used in the design of an isolated concrete footing which supports a column, pedestal or wall, shall be the moment computed by passing through a vertical section which extends completely across the footing at sections located as follows:

- (i) At the face of the column, pedestal or wall, for footings supporting a concrete column, pedestal or wall
- (ii) Halfway between the centre-line and the edge of the wall, for footings under masonry walls
- (iii) Halfway between the face of the column or pedestal and the edge of the gusseted base, for footings under gusseted bases.

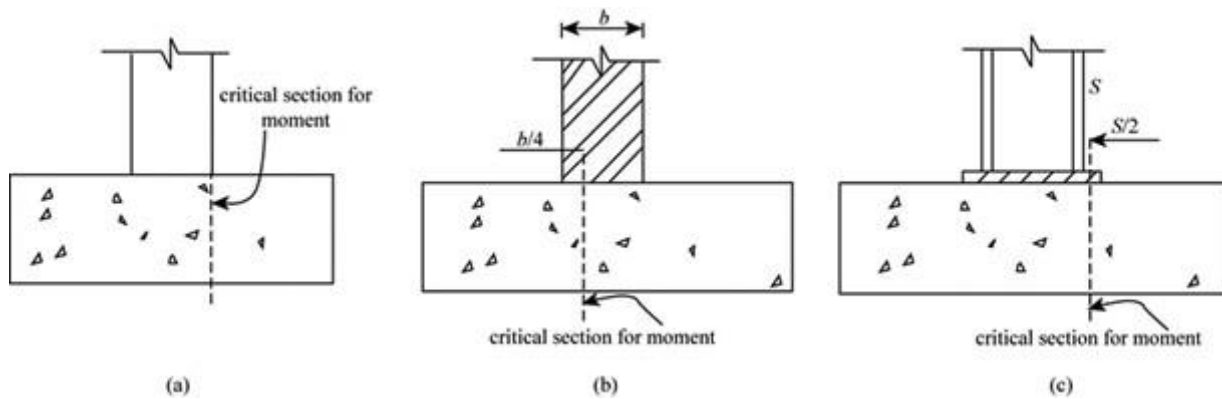

### Nominal reinforcement:

- Nominal reinforcement equal to 0.15% of gross cross sectional area for mild steel and 0.12% of gross cross sectional area for HYSD bars shall be considered as minimum reinforcement.
- The spacing of these reinforcement shall not exceed  $3d$  or  $300$  mm whichever is smaller for main bars and  $5d$  or  $450$  mm whichever is smaller for secondary bars.

### Critical section for Shear :

Two checks for shear are required:

#### One way shear:

- The sum of the vertical forces due to soil pressure on footing outside the critical section is called one way shear.
- The critical section for one way shear shall be assumed a vertical section located from the face of the column, pedestal or wall at a distance equal to the effective depth of footing in case of footing on soil and a distance equal to half the effective depth of footing for footing on piles.

#### Two way shear:

- The sum of vertical loads outside the appropriate perimeter is known as two-way shear.
- The critical section for shear in this case is at a distance  $d/2$  from the periphery of the column or pedestal where  $d$  is the effective depth of footing.
- The design shear strength in this case shall be taken equal to  $k_s \tau_c$

Where  $k_s = (0.5 + \beta_c)$  but not greater than 1,  $\beta_c$  being the ratio of short side to long side of the column

$$\tau_c = 0.25\sqrt{f_{ck}}$$

### Development length:

The critical section for checking the development length in footing shall be assumed at the same plane as those described for bending moment and also at all other vertical planes where abrupt changes of section occur.

### Deflection :

It is not important in footing and may not be checked.

**Reinforcement requirement:**

The following are the general reinforcement requirements for footings:

**Bending moment :** The total tensile reinforcement shall be distributed across the corresponding resisting section as given below:

- (i) In one – way reinforced footing and two – way reinforced square footing the reinforcement should be distributed uniformly across the full width of the footing.
- (ii) In two-way reinforced rectangular footing, the reinforcement in the long direction shall be distributed uniformly across the full width of footing.

For reinforcement in the short direction, a central band equal to width of footing shall be marked along the length of footing and portion of the reinforcement determined in accordance with the equation given below should be uniformly distributed across the central band:

$$\frac{\text{reinforcement in central band width}}{\text{total reinforcement in short direction}} = \frac{2}{\beta+1}$$

Where  $\beta$  is the ratio of the long side to the short side of the footing. The remainder of the reinforcement shall be uniformly distributed in the outer portion of the footing.

**Shear force:**

One – way shear check is made at a distance  $d$  from the face of the column. From this point, the bar must extend upto a minimum distance of  $d_1$ , where  $d_1$  is the effective depth of footing at a critical section for checking one – way shear. This is required as the design shear strength is based on percentage reinforcement at a section continuing at least for a distance of  $d_1$ .

**Development length:**

From the point of maximum bending moment, the bar must extend in both directions for a length equal to its development length. Generally mild steel reinforcement is provided with U bend anchorage while HYSD reinforcement is provided without end anchorage.

**Question 1:**

An R.C.C column of size 350 mm × 350 mm reinforced with 8 nos. 16 mm diameter bars carries a characteristic load of 800 KN. The allowable bearing pressure on soil is 200 KN/m<sup>2</sup>. Design an isolated square footing. The materials are grade M<sub>20</sub> concrete and HYSD reinforcement of grade Fe 415 for both the column and footing.

**Solution :****Size of footing:**

Load on column = 800 KN

Assume dead load of footing (10% of column load) = 80 KN

Total load on soil = 880 KN

Area of footing required =  $\frac{880}{200} = 4.4 \text{ m}^2$

Adopt 2.1 m × 2.1 m footing


Area = 4.41 m<sup>2</sup>

**Net upward pressure:**

Net factored upward pressure =  $\frac{1.5 \times 800}{2.1 \times 2.1} = 272.1 \text{ KN/m}^2$

Note that the weight of footing does not induce any shear or moment as the footing dead load is in opposite direction to the soil pressure. Thus in calculating the net upward pressure, only column load is considered.

#### Moment steel :

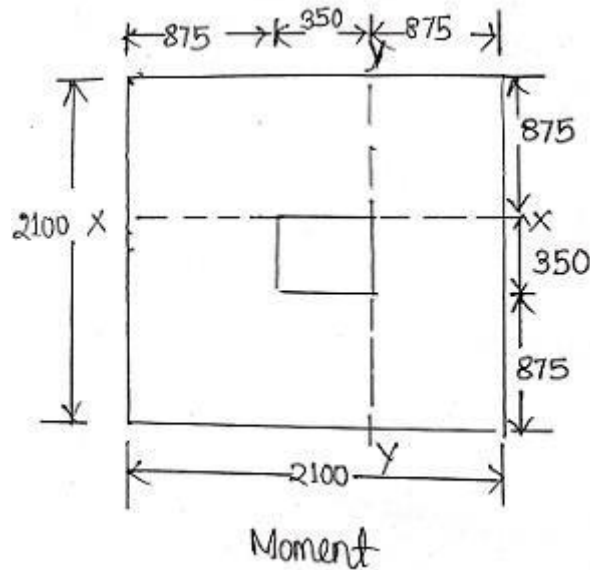

$$\text{Net cantilever} = \frac{2100 - 350}{2} = 875 \text{ mm}$$

$$M_{ux} = M_{uy} = \frac{0.875^2}{2} \times 272.1 \times 2.1 = 218.74 \text{ KN/m}$$

$$\text{Balanced depth required} = \sqrt{\frac{218.74 \times 10^6}{2100 \times 2.76}} = 194.3 \text{ mm}$$

Try an overall depth of 480 mm.

Assuming 12 mm diameter bars

$$d_x = 480 - 50 - 6 = 424 \text{ mm}$$

$$d_y = 424 - 12 = 412 \text{ mm (second layer)}$$

$$\frac{M_u}{bd^2} = \frac{218.74 \times 10^6}{2100 \times 2.76} = 0.614$$

$$p_t = 0.177$$

$$A_{st} = \frac{0.177 \times 2100 \times 412}{100} = 1531 \text{ mm}^2$$

$$\text{Minimum steel} = \frac{0.12 \times 2100 \times 500}{100} = 1260 \text{ mm}^2$$

Provide 14 nos. of 12 mm diameter = 1582 mm<sup>2</sup> on both the direction.

#### Development length:

$$\text{Development length} = 47\phi = 47 \times 12 = 564 \text{ mm}$$

$$\text{Available anchorage} = 875 - 50 (\text{cover}) = 825 \text{ mm} > 564 \text{ mm}$$

#### One way shear:


$$\text{Shear at 412 mm from face of the column} = 0.463 \times 2.1 \times 272.1 = 264.56 \text{ KN}$$

$$\tau_v = \frac{264.56 \times 10^3}{2100 \times 412} = 0.306 \text{ N/mm}^2 \quad (\text{Safe})$$

The bars extend 463 - 30 (side cover) = 413 mm, i.e more than d, beyond the critical section. Therefore, the steel is effective in increasing the shear stress.

$$\frac{100A_s}{bd} = \frac{100 \times 1582}{2100 \times 412} = 0.183$$

$$\tau_c = 0.306 \text{ N/mm}^2$$

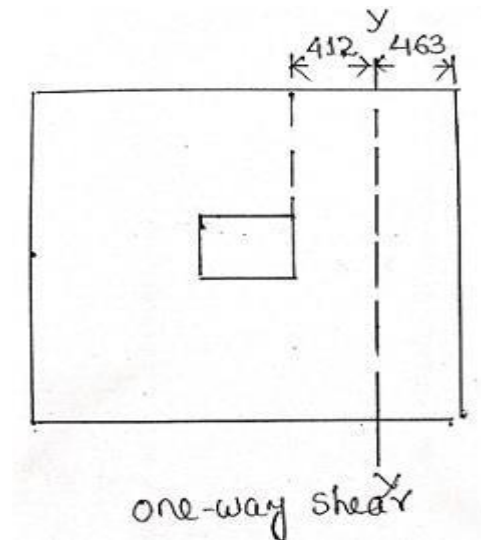

### Two – way shear:

This is checked at  $d/2$  from the face of the column

Here,  $d_x = 424 \text{ mm}$

$d_y = 412 \text{ mm}$

$d_{avg} = 0.5(424 + 412) = 418 \text{ mm}$

$V_u = (2.1^2 - 0.768^2) \times 272.1 = 1040 \text{ KN}$

$d = 418 \text{ mm}$

$b = 4 \times 768 = 3072 \text{ mm}$

$$\tau_v = \frac{1040 \times 10^3}{3072 \times 412} = 0.821 \text{ N/mm}^2$$

design shear strength =  $k_s \tau_c$

where  $k_s = 0.5 + \beta_c$

and  $\beta_c = \frac{\text{short side of column}}{\text{long side of column}} = \frac{1}{1} = 1$

$$k_s = 0.5 + 1 = 1.5$$


$k_s \leq 1$

$$k_s = 1$$

$$\tau_c = 0.25 \sqrt{f_{ck}} = 0.25 \sqrt{20} = 1.12 \text{ N/mm}^2$$

$$k_s \tau_c = 1 \times 1.12 = 1.12 \text{ N/mm}^2$$

$$\tau_v < k_s \tau_c \quad (\text{safe})$$

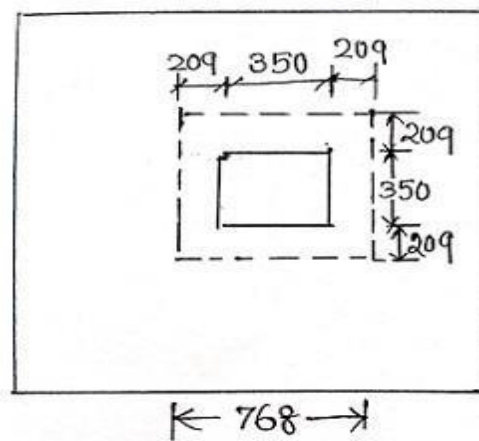

Two-way shear

### Spacing of bar:

$$\text{Spacing of bars} = \frac{2100 - 100 - 12}{13} = 152.92 \text{ mm} < 3 \times 432 (= 1296 \text{ mm}) \text{ or } 300 \text{ mm}$$

### Transfer of load from column to footing:

At the base of the column

$$\text{Allowable bearing force} = 0.45 \times 20 \times 350 \times 10^{-3} = 1102.5 \text{ KN} < 1200 \text{ KN}$$

$$\text{Force in dowel bars} = 1200 - 1102.5 = 97.5 \text{ KN}$$

At the top of footing:

$$A_1 = 2.1 \times 2.1 = 4.41 \text{ m}^2$$

$$A_1 = (0.35 + 4 \times 0.48)(0.35 + 4 \times 0.48) = 5.15 \text{ m}^2, \text{ whichever is small i.e } 4.41 \text{ m}^2$$

$$A_2 = 0.35 \times 0.35 = 0.12 \text{ m}^2$$

$$\sqrt{(A_1/A_2)} = 6.62, \text{ therefore use } 2$$

$$\text{Allowable bearing force} = 2 \times (0.45 \times 20) \times 350 \times 350 \times 10^{-3} = 2205 \text{ KN} \quad (\text{safe})$$



$$\text{Dowel area} = \frac{97.5 \times 10^3}{0.75 \times 415} = 313 \text{ mm}^2$$

$$\text{Minimum dowel area} = \frac{0.5 \times 350 \times 350}{100} = 612.5 \text{ mm}^2$$

Use 8 nos of 16 # column bars as dowel bars.

$$\text{Dowel length in footing} = D + 450 = 950 \text{ mm}$$





Extend column bars for 950 mm in footing.

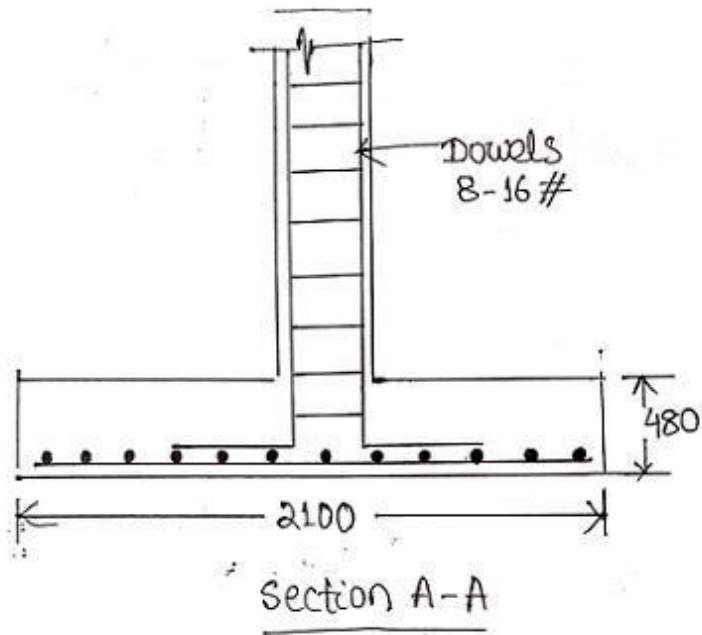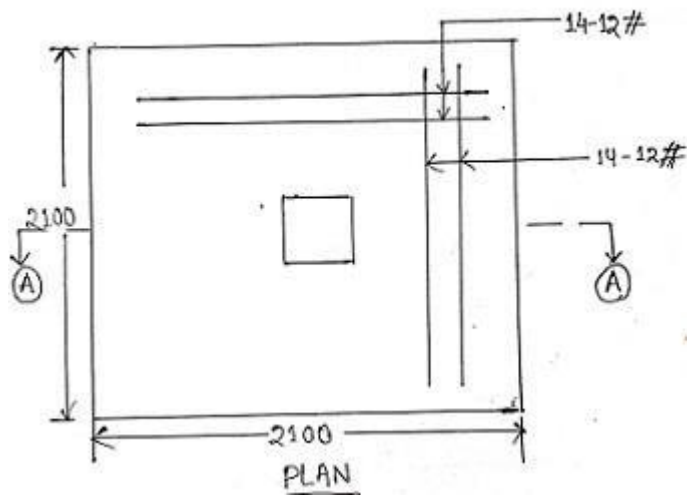

## Design of staircase

### Introduction:

- Functionally the staircase is an important component of a building and often the only means of access between the various floors in the building.
- It consists of a flight of steps, usually with one or more intermediate landings (horizontal slab platform) provided between the floor levels.
- The horizontal top portion of a step (where the foot rests) is termed as tread and the vertical projection of the step (i.e the vertical distance between two neighbouring steps) is called riser.
- Values of 300 mm and 150 mm are ideally assigned to the tread and riser respectively.
- The width of the stair is generally around 1.1 to 1.6 m.
- The horizontal projection (plan) of an inclined flight of steps, between the first and last risers is termed as going.
- Generally risers in a flight should not exceed about 12 in number.
- The steps in the flight can be designed in a number of ways: **with waist slab, with tread – riser arrangement (without waist slab) or with isolated tread slab.**

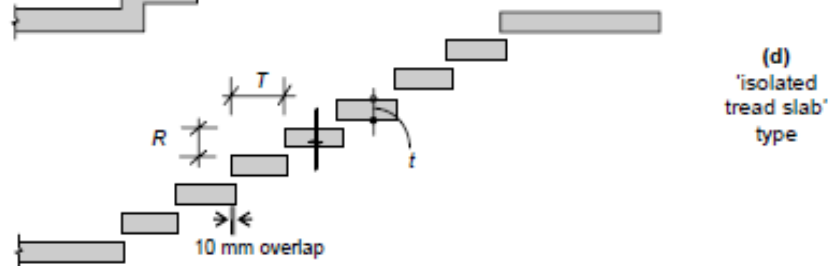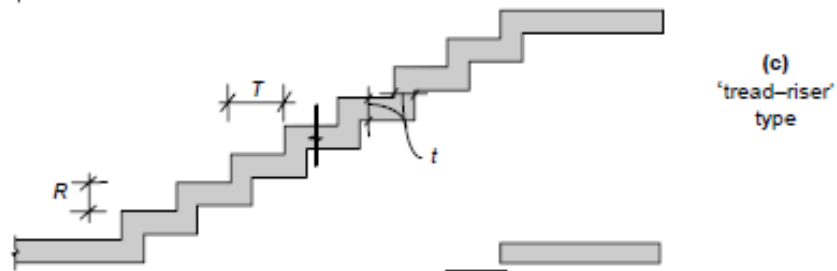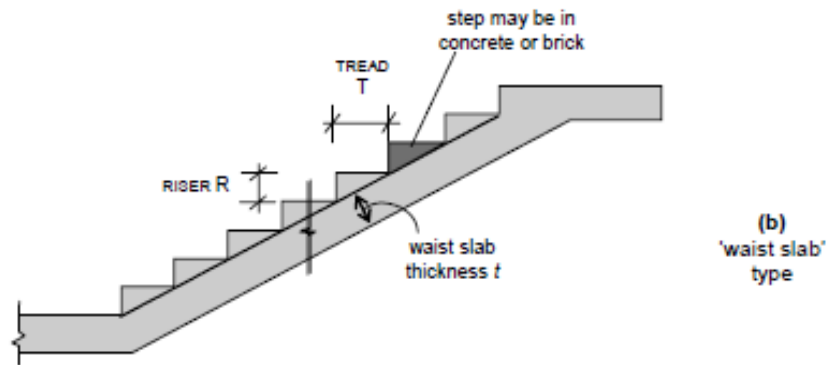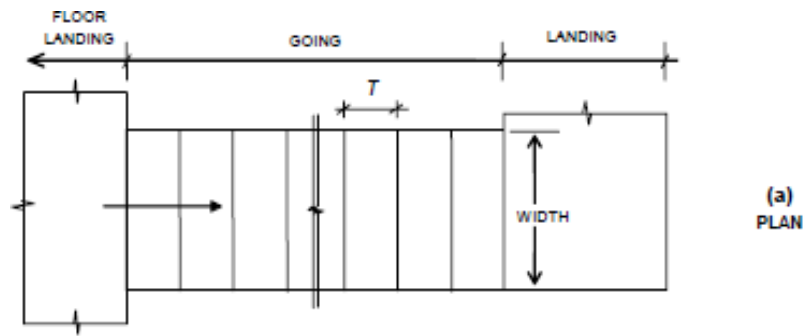


## Types of staircase:

### (a) Geometrical configuration:

These include:

- (1) Straight stair
- (2) Quarter turn stair
- (3) Dog legged stair
- (4) Open well stair
- (5) Spiral stair
- (6) Helicoidal stair

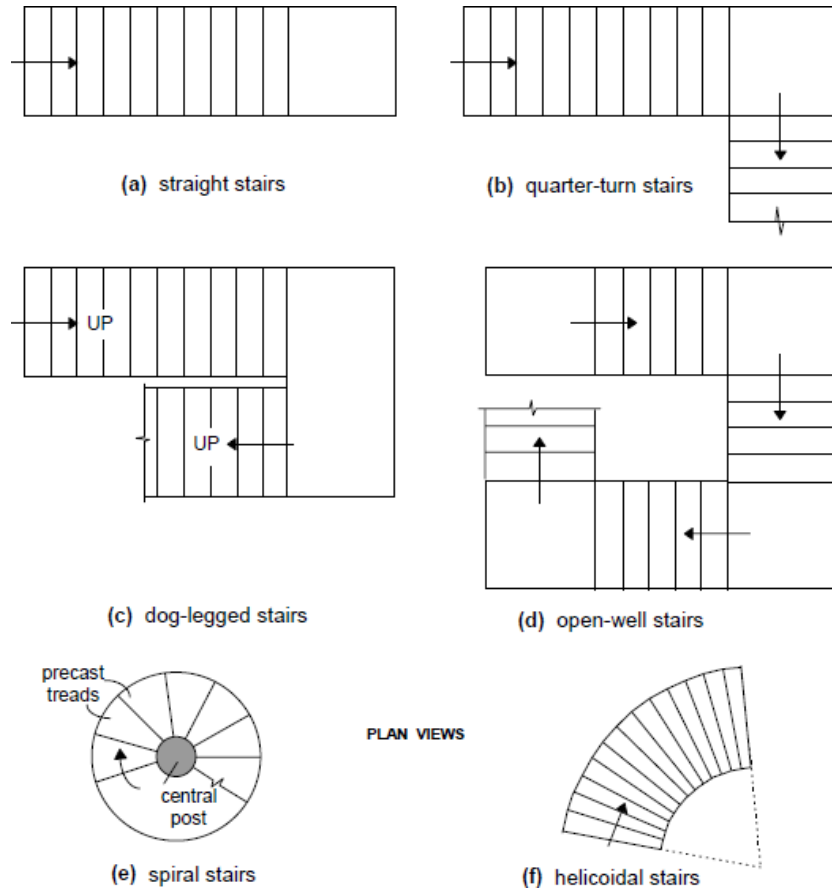

## (b) Structural Classification:


Structurally staircases may be classified largely into two categories, depending on the predominant direction in which the slab component of the stair undergoes flexure:

- (1) Stair slab spanning transversely (stair widthwise)
- (2) Stair slab spanning longitudinally (along the incline)

### Stair slab spanning transversely:

This category generally includes:


- (1) Slab cantilevered from a spandrel beam or wall
- (2) Slab doubly cantilevered from a central spine beam
- (3) Slab supported between two stringer beam or wall

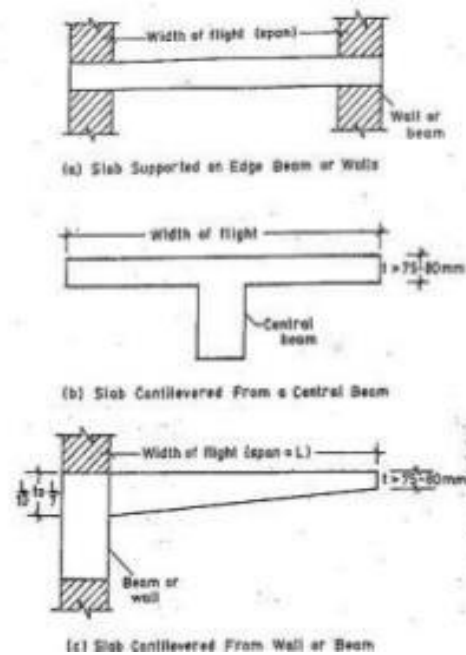

### Stair slab spanning longitudinally:

In this case, the support to the stair slab are provided parallel to the riser at two or more location, causing the slab to bend longitudinally between the supports. The slab arrangement may either be the conventional “waist slab type” or the “tread riser” type. The slab thickness depends on the “effective span” which should be taken as the centre to centre distance between the beam or wall support according to the code (Clause 33.1 a,c)

In certain situations, beam or wall supports may not be available parallel to the riser at the landing. Instead, the flight is supported between the landings, which span transversely, parallel to the riser. In such cases, the code (Cl. 33.1 b) specifies that the effective span for the stairs (spanning longitudinally) should be taken as the “going of the stair plus at each end either half the width of the landing or one metre, whichever is smaller”

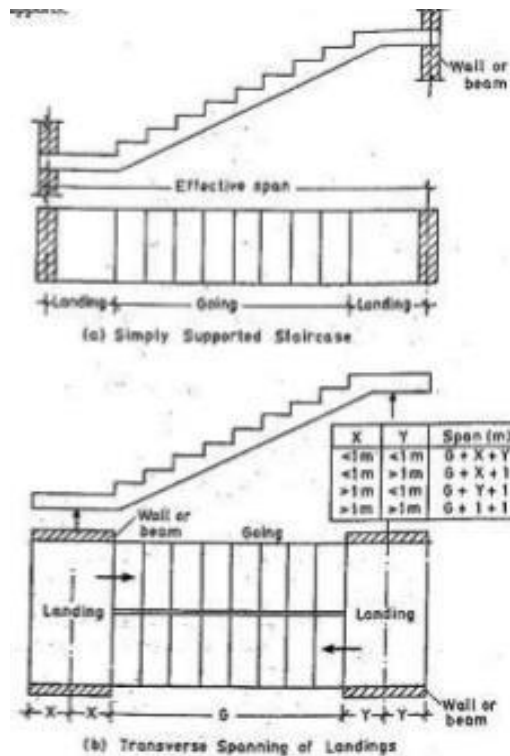

### Loads on stair slabs:

Stair slabs are usually designed to resist gravity loads, comprising dead load and live load.

Dead loads:

The components of the dead load to be considered comprise:

- Self weight of the stair slab
- Self weight of step
- Self weight of tread finish (usually 0.5 to 1.0 KN/m<sup>2</sup>)

Live loads:

- Live loads are generally assumed to act as uniformly distributed loads on the horizontal projection of the flight, i.e on the going. The loading code (IS 875 : 1987 (part II)) recommends a uniformly distributed load of 5.0 KN/m<sup>2</sup> on the going as well as landing.
- However in buildings (such as residences) where the specified floor live loads do not exceed 2.0 KN/m<sup>2</sup> and the staircases are not liable to be overcrowded, the loading code recommends a lower live load of 3.0 KN/m<sup>2</sup>.
- Further in case of structurally independent cantilever steps, the loading code requires the tread slab to be capable of safely resisting a concentrated live load of 1.3 KN applied to the free end of each cantilevered tread.

### Question 1:

Design a (waist slab type) dog legged staircase for an office building, given the following data

Height between floor = 3.2 m

Riser = 160 mm, tread = 270 mm

Width of flight = landing width = 1.25 m

Live load = 5.0 KN/m<sup>2</sup>

Finish load = 0.6 KN/m<sup>2</sup>

Assume the stairs to be supported on 230 mm thick masonry walls at the outer edges of the landing parallel to the risers. Use M20 concrete and Fe415 grade steel

**Solution:**

Given R = 160 mm

T = 270 mm

$$\sqrt{(R^2 + T^2)} = 314 \text{ mm}$$

Effective span = c/c distance between supports = 5.16 m

Assume a waist slab thickness =  $l/20 = 5160/20 = 258$  or 260 mm

Assuming 20 mm clear cover and 12 # main bars

Effective depth =  $d = 260 - 20 - (12/2) = 234$  mm

The slab thickness in the landing regions may be taken as 200 mm as the bending moment is relatively low here.

**Loads on going:** on projected plan area

(1) Self weight of waist slab =  $25 \times 0.26 \times (314/270) = 7.56 \text{ KN/m}^2$

(2) Self weight of steps =  $25 \times (0.16/2) = 2.00 \text{ KN/m}^2$

(3) Finishes = 0.6 KN/m<sup>2</sup>

(4) Live load (given) = 5.00 KN/m<sup>2</sup>

Total load = 15.16 KN/m<sup>2</sup>

Factored load =  $15.16 \times 1.5 = 22.74 \text{ KN/m}^2$

**Loads on landing:**

(1) Self weight of slab =  $25 \times 0.2 = 5.00 \text{ KN/m}^2$

(2) Finishes = 0.6 KN/m<sup>2</sup>

(3) Live loads = 5.00 KN/m<sup>2</sup>

Total load = 10.60 KN/m<sup>2</sup>

Factored load =  $10.60 \times 1.5 = 15.90 \text{ KN/m}^2$

Design moment:

Reaction R =  $(15.90 \times 1.365) + (22.74 \times 2.43)/2 = 49.33 \text{ KN/m}$

$$\begin{aligned} \text{Maximum moment at mid span} = M_u &= (49.33 \times 2.58) - (15.90 \times 1.365) \times (2.58 - 1.365/2) \\ &\quad - (22.74) \times (2.58 - 1.365)^2 \\ &= 69.30 \text{ KNm/m} \end{aligned}$$

**Main reinforcement :**

$$M_u = 0.87 f_y A_{st} (d - 0.42 x_u)$$

$$69.30 \times 10^6 = 0.87 \times 415 \times A_{st} (234 - 0.42 \times 0.48 \times 234)$$

$$A_{st} = 1027.35 \text{ mm}^2$$

$$\text{Required Spacing} = \frac{1000 \times \text{area of one bar}}{\text{required area}} = \frac{1000 \times \frac{\pi d^2}{4}}{A_{st}} = \frac{1000 \times 113}{1027.35} = 110 \text{ mm}$$

Provide 12 mm dia bars @ 110 mm c/c

**Distribution reinforcement:**

$$A_{st} = \frac{0.12 \times 1000 \times 234}{100} = 280 \text{ mm}^2$$

$$\text{Spacing} = \frac{1000 \times \text{area of one bar}}{\text{required area}} = \frac{1000 \times \frac{\pi d^2}{4}}{A_{st}} = \frac{1000 \times 78.54}{280} = 280.5 \text{ mm}$$

Provide 10 mm dia bars @ 250 mm c/c.

Some nominal reinforcement (10 mm dia bars @ 110 mm c/c) is provided in the landing slab near the support at top to resist possible negative bending moment and 8 mm dia bars @ 250 mm c/c are also provided as distribution reinforcement.



